

## Operator DEFI\_GLRC

---

### 1 Goal

---

The operator `DEFI_GLRC` permit to define the parameters of the models of reinforced concrete behavior `GLRC_DAMAGE` [R7.01.31] and `GLRC_DM` [R7.01.32].

It makes it possible to determine the characteristics of the reinforced concrete homogenized starting from the properties of the concrete and several types of reinforcement (passive reinforcements, cables of prestressing, liner metal).

In this order, one informs the physical properties (elastic, yield stress coefficients) and geometrical (steel section and positions) of the reinforced concrete. At exit, one lays out of a concept "material", which one can then assign to the various meshes of plates with the order `AFFE_MATERIAU`.

It is important to note that before calling on `DEFI_GLRC`, it is necessary to use `DEFI_MATERIAU` or `DEFI_MATER_GC` to inform the whole of the parameters material concerning the concrete and steel components.

Product a Structure of data of the type `to subdue`.

## Contents

1 Goal.....	1
2 General syntax.....	4
3 General description of the reinforced concrete hull.....	6
4 Operands RELATION = GLRC_DM.....	7
4.1 Keyword CONCRETE.....	7
4.1.1 Operand MATER.....	7
4.1.2 Operand THICK.....	7
4.2 Keyword TABLECLOTH.....	7
4.2.1 Operand MATER.....	7
4.2.2 Operands OMX and OMY.....	7
4.2.3 Operands X-ray and RY.....	8
4.3 Operand RHO.....	8
4.4 Operands AMOR_ALPHA, AMOR_BETA and AMOR_HYST.....	8
4.5 Keyword factor SLOPE.....	9
4.5.1 Operand TRACTION.....	9
4.5.2 Operand INFLECTION.....	10
4.5.3 Operand EPSI_MEMB.....	11
4.5.4 Operand KAPPA_FLEX.....	11
4.6 Keyword CISAIL.....	12
4.7 Keyword INFORMATION.....	12
4.8 Example of use.....	12
5 Operands RELATION = GLRC_DAMAGE.....	13
5.1 Keyword CONCRETE.....	13
5.1.1 Operand MATER.....	13
5.1.2 Operand THICK.....	13
5.1.3 Operand GAMMA.....	13
5.1.4 Operands QP1 and QP2.....	15
5.1.5 Operands C1N1/C1N2/C1N3/C2N1/C2N2/C2N3.....	15
5.1.6 Operands C1M1/C1M2/C1M3/C2M1/C2M2/C2M3.....	15
5.1.7 Operands BT1/BT2 and EAT/OMT.....	16
5.1.8 Operands MP1X/MP1Y/MP2X/MP2Y and MP1X_FO/MP1Y_FO/MP2X_FO/MP2Y_FO...17	
5.2 Keyword ARMED.....	17
5.2.1 Operand MATER.....	17
5.2.2 Operands OMX and OMY.....	17
5.2.3 Operands X-ray and RY.....	17
5.3 Keyword CABLE_PREC.....	18
5.3.1 Operand MATER.....	18
5.3.2 Operands OMX and OMY.....	18

5.3.3 Operands X-ray and RY.....	18
5.3.4 Operands PREX and PREY.....	18
5.4 Keyword LINER.....	19
5.4.1 Operand MATER.....	19
5.4.2 Operand OML.....	19
5.4.3 Operand RLR.....	19
5.5 Keyword ALPHA.....	19
5.6 Keyword INFORMATION.....	19
6 Example of use.....	20

## 2 General syntax

```

my [to subdue] = DEFI_GLRC (
reuse      = chechmate,                                [to subdue]
◆ RELATION = / GLRC_DM
# Definition of the parameters concrete
  ◆ CONCRETE = ( _F (◆ MATER = mat_beton,             [to subdue]
                  ◆ THICK   = ep,                    [R]
                  ),
# Definition of the parameters of the reinforcements
  ◆ TABLECLOTH = ( _F (◆ MATER = mat_acier,         [to subdue]
                       ◆ OMX   = Wx,                 [R]
                       ◆ OMY   = Wy,                 [R]
                       ◆ X-ray  = X-ray,              [R]
                       ◆ RY     = ry,                 [R]
                       ),
  ◆ RHO          = rho                                [R]
  ◆ AMOR_ALPHA   = amor_alpha                         [R]
  ◆ AMOR_BETA    = amor_beta                          [R]
  ◆ AMOR_HYST    = amor_hyst                          [R]

  ◆ SLOPE = _F (◆ TRACTION = / RIGI_ACIER            [DEFECT]
                / PLAS_ACIER
                / UTIL
                # if TRACTION = UTIL
                ◆ EPSI_MEMB = EM,                    [R]

                ◆ INFLECTION = / RIGI_INIT            [DEFECT]
                / RIGI_STEEL
                / PLAS_STEEL
                / UTIL
                # if INFLECTION = UTIL
                ◆ KAPP_FLEX = KF,                    [R]

  ◆ CISAIL = / YES
             / NOT                                  [DEFECT]
  ◆ INFO= / 1
           / 2                                  [DEFECT]

◆RELATION = / GLRC_DAMAGE
# Definition of the parameters concrete
  ◆ CONCRETE = ( _F (◆ MATER = mat_beton,             [to subdue]
                  ◆ THICK = ep,                      [R]
                  ◆ GAMMA = gamma,                   [R]
                  ◆ QP1   = qp1,                     [R]
                  ◆ QP2   = qp2,                     [R]

                  ◆ C1N1  = c1n1,                    [R]
                  ◆ C1N2  = c1n2,                    [R]
                  ◆ C1N3  = c1n3,                    [R]
                  ◆ C2N1  = c2n1,                    [R]
                  ◆ C2N2  = c2n2,                    [R]
                  ◆ C2N3  = c2n3,                    [R]
                  ◆ C1M1  = c1m1,                    [R]
                  ◆ C1M2  = c1m2,                    [R]
                  ◆ C1M3  = c1m3,                    [R]
                  ◆ C2M1  = c2m1,                    [R]
                  ◆ C2M2  = c2m2,                    [R]

```

```

    ◆ C2M3 = c2m3, [R]

    ◇ BT1 = bt1, [R]
    ◇ BT2 = bt2, [R]

    ◇ EAT = eat, [R]
    ◇ OMT = omt, [R]

    ◇ MP1X = mp1x, [1_R]
    ◇ MP1Y = mp1y, [1_R]
    ◇ MP2X = mp2x, [1_R]
    ◇ MP2Y = mp2y, [1_R]

    ◇ MP1X_FO = mp1x_fo, [1_R]
    ◇ MP1Y_FO = mp1y_fo, [1_R]
    ◇ MP2X_FO = mp2x_fo, [1_R]
    ◇ MP2Y_FO = mp2y_fo, [1_R]
),

# Definition of the parameters passive reinforcements
◆ TABLECLOTH = ( _F ( ◆ MATER = mat_acier, [to subdue]
    ◆ OMX = Wxa, [R]
    ◆ OMY = Wya, [R]
    ◆ X-ray = rxa, [R]
    ◆ RY = rya, [R]
),

# Definition of the parameters cables of prestressing
◆ CABLE_PREC = ( _F ( ◆ MATER = mat_cable, [to subdue]
    ◆ OMX = Wxp, [R]
    ◆ OMY = Wyp, [R]
    ◆ X-ray = rxp, [R]
    ◆ RY = ryp, [R]
    ◆ PREX = precx, [R]
    ◆ PREY = precy, [R]
),


# Definition of the parameters liner metal
◆ LINER = ( _F ( ◆ MATER = mat_liner, [to subdue]
    ◆ OML = W L, [R]
    ◆ RLR = rlr, [R]
),

# Definition of the thermal dilation coefficient "average":
◇ ALPHA = alpha, [R]

◇ INFORMATION =/ 1 [DEFECT]
/ 2
)
```

## 3 General description of the reinforced concrete hull

One describes in this paragraph the geometry of the hull considered.

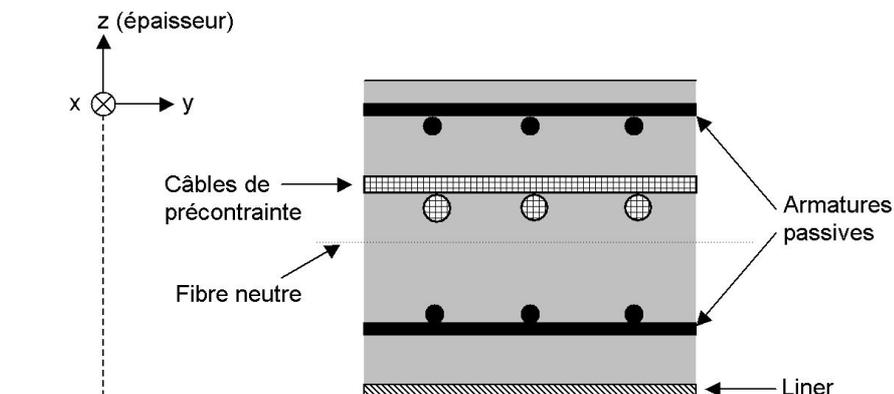

**Figure 3-a: Current section of the reinforced concrete hull.**

The basic section of a reinforced concrete flagstone (Figure 3-a) is made up:

- concrete hull
- passive reinforcements

and in the case of `GLRC_DAMAGE`, the section can contain moreover:

- cables of prestressing
- a metal liner

The liner is a steel plate placed in internal skin of the enclosure guaranteeing the sealing in the event of accidental escape in particular.

Prestressing makes it possible to compress the structural concrete of civil engineer. This prestressing is applied using cables of prestressed out of steel energized.

## 4 Operands RELATION = GLRC\_DM

The documentation of the model will be consulted `GLRC_DM` [R7.01.32].

### 4.1 Keyword CONCRETE

The keyword factor `CONCRETE` allows to define the geometrical characteristics and material of the concrete.

#### 4.1.1 Operand MATER

`MATER = mat_beton`

The name of material produced defines obligatorily by `DEFI_MATER_GC/BETON_GLRC` used for the concrete. This operand makes it possible to check that the parameters associated with the behaviors concrete exist well in material.

#### 4.1.2 Operand THICK

`THICK = ep`

The thickness of the concrete plate defines. It is checked that  $ep \geq 0$ .

Note:

The value this thickness must be identical to that given in `AFFE_CARA_ELEM` for the elements of hull using material `mat_beton` (defined by `DEFI_GLRC`).

### 4.2 Keyword TABLECLOTH

The keyword factor `TABLECLOTH` allows to define the geometrical characteristics and material of the passive reinforcements. This keyword can be defined only once. Indeed, under the assumption of isotropy in elasticity of the law of behavior `GLRC_DM`, all the reinforcements are necessarily identical and to equidistance of neutral fibre.

#### 4.2.1 Operand MATER

`MATER = mat_acier`

The name of material produced defines obligatorily by `DEFI_MATER_GC/ACIER` used for the passive reinforcements.

This operand makes it possible to recover the parameters material used for the passive reinforcements (Young modulus  $E_a$ , Poisson's ratio  $\nu_a$  and yield stress  $\sigma_{ya}$ ).

#### 4.2.2 Operands OMX and OMY

`OMX = wx`

`OMY = wy`

Define the steel sections  $\Omega_x$  and  $\Omega_y$  of any of the two beds of reinforcements given according to the directions  $x$  and  $y$  (in  $m^2/m$  linear if the thickness is given in  $m$ ). It is pointed out that the formulation of the model `GLRC_DM` impose that the two tablecloths of reinforcements are identical.

It is checked that  $\Omega_x > 0$  and  $\Omega_x = \Omega_y$ . With the two tablecloths of reinforcements in the reinforced concrete section, there will be thus a rate of total reinforcement equal to  $2\Omega_x = 2\Omega_y$ .

## 4.2.3 Operands X-ray and RY

X-ray = X-ray  
RY = ry

Define the position adimensionnée of a bed of reinforcements compared to the thickness of the concrete hull, given in the directions  $x$  and  $y$  ( $-1 \leq rx \leq 1$ ,  $-1 \leq ry \leq 1$ , Figure 4.2.3-a).

It is checked that  $rx = ry$ .

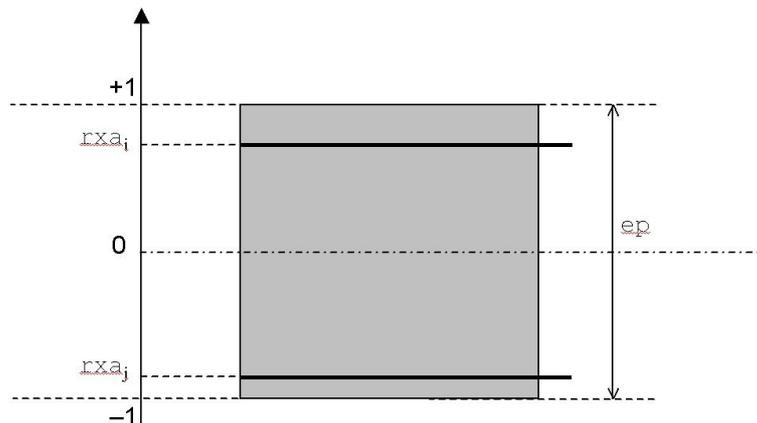


Figure 4.2.3-a: Définition of the adimensionnée position of the beds of reinforcements.

## 4.3 Operand RHO

RHO = rho

Operand optional allowing the user to define the equivalent density of the reinforced concrete flagstone. If the operand is not defined, the density is calculated in the following way:

$$\rho_{eq} = \rho_b + \frac{\rho_a}{h} (\Omega_x^{sup} + \Omega_x^{inf} + \Omega_y^{sup} + \Omega_y^{inf})$$

Where  $\rho_a$  indicate the density of steel and is recovered in the concept `mat_acier` provided by the operand `MATER` keyword `TABLECLOTH`.

Where  $\rho_b$  indicate the density of the concrete and is recovered in the concept `mat_beton` provided by the operand `MATER` keyword `CONCRETE`.

Where  $h$  is the thickness provided by the keyword `THICK`.

## 4.4 Operands AMOR\_ALPHA, AMOR\_BETA and AMOR\_HYST

AMOR\_ALPHA = amor\_alpha  
AMOR\_BETA = amor\_beta  
AMOR\_HYST = amor\_hyst

Operand optional allowing the user to define the coefficients  $\alpha$  and  $\beta$  who are used to build the matrix of the damping of Rayleigh and  $\eta$  for damping hysteretic.

$$C = \alpha K + \beta M$$

One will refer to the documents of modeling of the mechanical cushioning [U2.06.03] and [R5.05.04].

If the operands are not indicated in the order, they take the values defined in the concept `mat_beton` provided by the operand `MATER` keyword `CONCRETE`.

## 4.5 Keyword factor SLOPE

### 4.5.1 Operand TRACTION

```
◇ TRACTION = / RIGI_ACIER [DEFECT]
              / PLAS_ACIER
              / UTIL
```

The keyword `TRACTION` allows to define the method of calculating of the slope post-rubber band. Indeed, it is possible to carry out this calculation according to three methods called `RIGI_ACIER`, `PLAS_ACIER` and `UTIL`. These three calculations of slopes make it possible to set up three different methods of retiming according to the properties materials informed for traction. If the yield stress of steels is not known, methods of retiming `RIGI_ACIER`, i.e slope post-rubber band equalizes with the slope of resumption of stiffness of steels, and `UTIL`, i.e slope post-rubber band cuts the slope of resumption of stiffness of steels to a maximum deformation whose value is imposed by the user, are accessible (cette method is not adapted for maximum deformations weaker than the hollow of the curve of reference, to see Figure 4.5.1-b). If the elastic limit of steels is known, it is possible to use the method of retiming to the plastic limit of steels (`PLAS_ACIER`). The various methods of retiming are illustrated by the figures which follow.

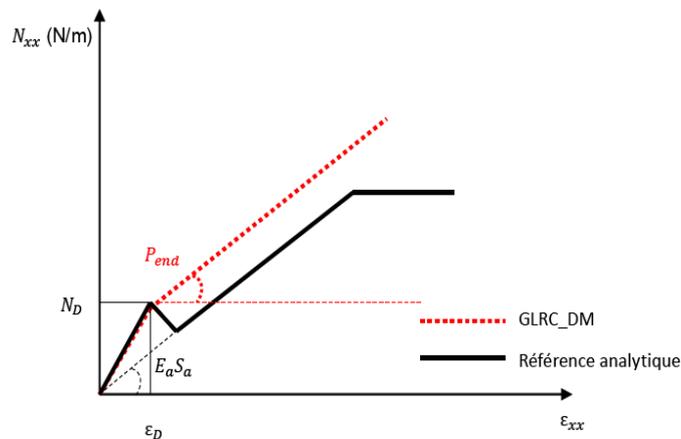


Figure 4.5.1-a: Traction diagram (GLRC\_DM vs Référence) Retiming SLOPE = RIGI\_ACIER

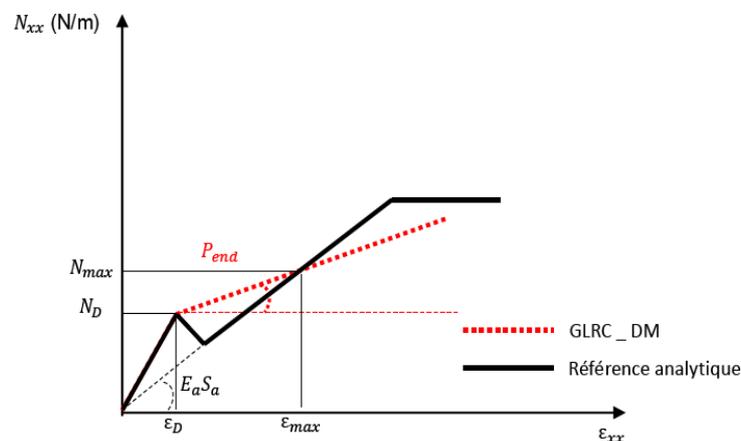


Figure 4.5.1-b: Traction diagram (GLRC\_DM vs Référence) Retiming SLOPE = UTIL

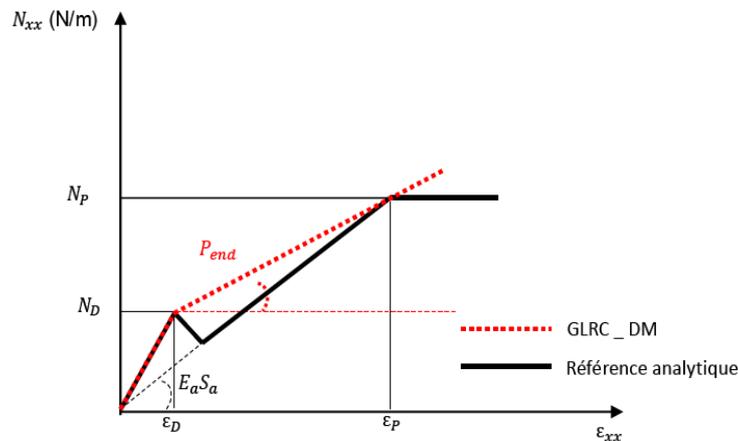


Figure 4.5.1-c: Traction diagram (GLRC\_DM vs Référence) Retiming SLOPE = PLAS\_ACIER

In the case of retiming with the maximum deformation (TRACTION=UTIL), it is necessary to inform the maximum deformation out of membrane (EPSI\_MEMB).

## 4.5.2 Operand INFLECTION

```

◇ INFLECTION =      / RIGI_INIT [DEFECT]
                   / RIGI_STEEL
                   / PLAS_STEEL
                   / UTIL
    
```

The keyword `INFLECTION` allows to define the method of calculating of the slope post-rubber band. Indeed, it is possible to carry out this calculation according to two methods called `RIGI_INIT`, `RIGI_ACIER`, `PLAS_ACIER` and `UTIL`.

Options `RIGI_ACIER` and `PLAS_ACIER` correspond to the parameter settings exposed for the inflection to 4.5.1, transposed to the case of the inflection.

In the case of the option `RIGI_INIT`, the bilinear approximation of answer in inflection of the section is given in the following way (cf [R7.01.32]):

- the threshold of élasticity is fixed for a value  $M$  which deviates from 5 % of the theoretical curve;
- the second slope is defined so that bilinear law that is to say tangent with the theoretical curve.

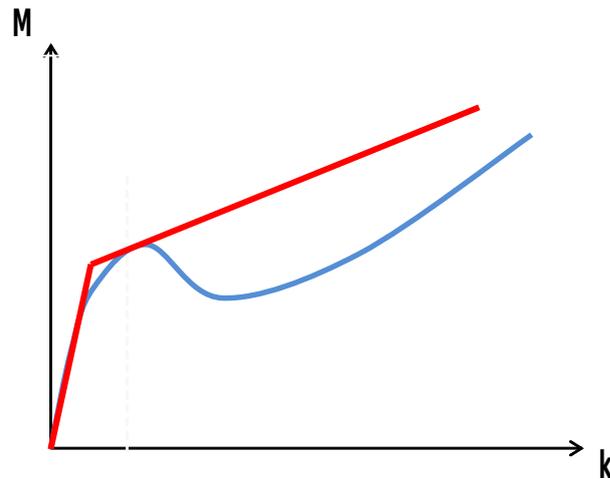


Figure 4.5.2-a: Curve of inflection (GLRC\_DM vs Référence) Retiming SLOPE = RIGI\_INIT

In the case of the option UTIL, the bilinear approximation of answer in inflection of the section is given in order to decrease the relative surface compared to the theoretical answer of the section until curve KF (KAPPA\_FLEX) . (cf [R7.01.32])

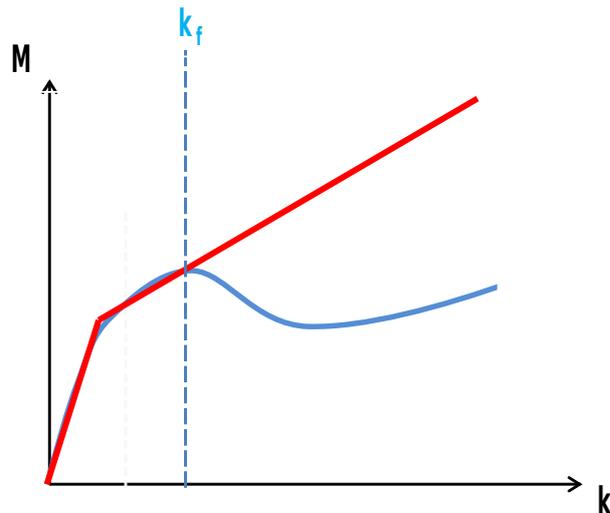


Figure 4.5.2-b: Curve of inflection (GLRC\_DM vs Référence) Retiming SLOPE = UTIL

### 4.5.3 Operand EPSI\_MEMB

EPSI\_MEMB = EM

The value of the maximum deformation out of membrane in the case defines TRACTION=UTIL .

### 4.5.4 Operand KAPPA\_FLEX

KAPPA\_FLEX = KF

Defines the value of the maximum curve in inflection (opposite a length) in the case FLEXION=UTIL .

## 4.6 Keyword CISAIL

The simple keyword `CISAIL` allows to determine whether the homogenized elastic parameters are those calculated by homogenisation for a standard application of the model of behavior (`CISAIL=NON`) or those calculated for a particular application in order to respect the fact when one is in shearing pure plan the rigidity of steels does not intervene in the elastic behavior (`CISAIL=OUI`).

## 4.7 Keyword INFORMATION

With `INFORMATION = 2`, one obtains the Impression with the format `RESULT` list of the homogenized parameters used as starter of the model of behavior `GLRC_DM`: elasticity, thresholds and damaging behavior.

## 4.8 Example of use

One will be able to consult the example of use deferred in the test `SSNS106A`, in situation of traction and compression, and in the test `SSNS106B`, in situation of alternating bending, cf [V6.05.106]. It can be used in order to check on the case to study the consequences in terms of answer for elementary loadings in alternate statics of the choice of the parameters and methods of identification.

## 5 Operands **RELATION = GLRC\_DAMAGE**

The documentation of the model will be consulted `GLRC_DAMAGE` [R7.01.31].

### 5.1 Keyword **CONCRETE**

The keyword factor `CONCRETE` allows to define the geometrical characteristics and material of the concrete.

#### 5.1.1 Operand **MATER**

`MATER = mat_beton`

The name of material produced defines by `DEFI_MATERIAU` used for the concrete. This operand makes it possible to check that the parameters associated with the behaviors chosen under the keywords `FLOW`, `ECRO_ISOT`, `ECRO_CINE` and `ELAS` exist well in material.

#### 5.1.2 Operand **THICK**

`THICK = ep`

The thickness of the concrete plate defines. It is checked that  $ep \geq 0$ .

Note:

The value this thickness must be identical to that given in `AFFE_CARA_ELEM` for the elements of hull using material `mat_beton` (defined by `DEFI_GLRC`).

#### 5.1.3 Operand **GAMMA**


`GAMMA = gamma`

The parameter of damage defines which characterizes the slope of the curved moment – curve during the cracking of the concrete (figure 2). *gamma* can be regarded as being the relationship between the slope lasting cracking on the elastic slope. If  $gamma > 0$ , the slope is positive. If  $gamma < 0$ , the slope decrease and stability is not guaranteed any more. In all the cases, we must have  $gamma < QP1$  and  $gamma < QP2$ . The value by default is 0. This parameter is used only for the calculation of the damage:

$$\gamma = \frac{p_f}{p_{\text{elas}}}$$

with:

- $\gamma$  : GAMMA
- $p_{\text{elas}}$  : elastic slope
- $p_f$  : slope during cracking

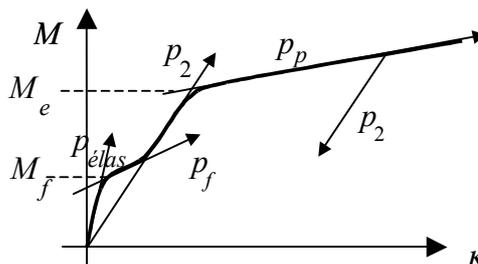

**Figure 5.1.3-a: Curve moment – curve of the behavior of a reinforced concrete plate in inflection.**

## 5.1.4 Operands QP1 and QP2

QP1 = qp1  
QP2 = qp2

Ratios of slopes for a positive or negative inflection define. The ratio is supposed to be the report of the slope of the curved curve – moment after cracking on the elastic slope. They are used only for the calculation of the damage:

$$Q_p = \frac{p_2}{p_{elas}}$$

With:

- $Q_p$  : ratio of the slopes
- $p_{elas}$  : elastic slope
- $p_2$  : slope after cracking

It is checked that  $0 < QP_i < 1$  .

## 5.1.5 Operands C1N1/C1N2/C1N3/C2N1/C2N2/C2N3

C1N1 = c1n1  
C1N2 = c1n2  
C1N3 = c1n3  
C2N1 = c2n1  
C2N2 = c2n2  
C2N3 = c2n3

The components of the kinematic tensor of work hardening of Prager define binding the tensors of the membrane plastic deformations with the efforts of kinematic membrane of recall.

$$N = CN_1 \epsilon_1^p + CN_2 \epsilon_2^p$$

With:

$$\bullet CN_1 = \begin{pmatrix} CIN1 & 0 & 0 \\ 0 & CIN2 & 0 \\ 0 & 0 & CIN3 \end{pmatrix}$$
$$\bullet CN_2 = \begin{pmatrix} C2N1 & 0 & 0 \\ 0 & C2N2 & 0 \\ 0 & 0 & C2N3 \end{pmatrix}$$

- $\epsilon_1^p$  and  $\epsilon_2^p$  are the tensors of membrane plastic deformation for the criterion of plasticity 1 and 2.

It is checked that  $CiN_j \geq 0$  .

## 5.1.6 Operands C1M1/C1M2/C1M3/C2M1/C2M2/C2M3

C1M1 = c1m1  
C1M2 = c1m2  
C1M3 = c1m3  
C2M1 = c2m1  
C2M2 = c2m2

C2M3 = c2m3

The components of the kinematic tensor of work hardening of Prager define binding the tensors of the plastic curves with the moments of kinematic recall.

$$M = CM_1 \kappa_1^p + CM_2 \kappa_2^p$$

With:

$$\bullet CM_1 = \begin{pmatrix} CIM1 & 0 & 0 \\ 0 & CIM2 & 0 \\ 0 & 0 & CIM3 \end{pmatrix}$$
$$\bullet CM_2 = \begin{pmatrix} C2M1 & 0 & 0 \\ 0 & C2M2 & 0 \\ 0 & 0 & C2M3 \end{pmatrix}$$

•  $\kappa_1^p$  and  $\kappa_2^p$  are the tensors of plastic curve for the criteria of plasticity 1 and 2.

The calculation of  $C_i M_j$  is carried out by using MOCO.

$$C_i M_j = \frac{p_{\text{élas}} p_p}{p_{\text{élas}} - p_p}$$

with:

- $p_{\text{élas}}$  : elastic slope
- $p_p$  : plastic slope

It is checked that  $C_i M_j \geq 0$ .

## 5.1.7 Operands BT1/BT2 and EAT/OMT

BT1 = bt1

BT2 = bt2

EAT = eat

OMT = omt

If the finite elements support the calculation of the efforts cutting-edges, these operands are used to define the elastic matrix of rigidity of transverse shearing. The efforts cutting-edges  $V$  are connected to the distortions  $\gamma$  by:

$$V = \begin{bmatrix} BT1 & 0 \\ 0 & BT2 \end{bmatrix} : \gamma$$

If the user informs the Young modulus of transverse steels EAT as well as the steel section transverse per linear meter OMT then one deduces the coefficients from the matrix of rigidity by the following relation:

$$bt_i = \frac{5}{6} \frac{ep}{2} \left( \frac{eb}{1+nub} + eat \times omt \right)$$

The user cannot inform at the same time BT1, BT2 and parameters EAT, OMT.

It is checked that these operands are strictly positive realities.

## 5.1.8 Operands MP1X/MP1Y/MP2X/MP2Y and MP1X\_FO/MP1Y\_FO/MP2X\_FO/MP2Y\_FO

```
MP1X = mp1x  
MP1Y = mp1y  
MP2X = mp2x  
MP2Y = mp2y
```

```
MP1X_FO = mp1x_fo  
MP1Y_FO = mp1y_fo  
MP2X_FO = mp2x_fo  
MP2Y_FO = mp2y_fo
```

The limiting plastic moments of the generalized criterion of Johansen used in the model of behavior define `GLRC_DAMA`. They can be defined by constant values or by functions. It is not possible to mix functions and constants. Moreover as soon as one of the operands is indicated, it is obligatory for all to inform them. When those are not specified, they are calculated in an automatic way.

## 5.2 Keyword ARMED

The keyword factor `ARMED` allows to define the geometrical characteristics and material of the passive reinforcements.

### 5.2.1 Operand MATER

```
MATER= mat_acier
```

The name of material produced defines by `DEFI_MATERIAU` used for the passive reinforcements. This operand makes it possible to recover the parameters material used for the passive reinforcements (Young modulus  $E_a$ , Poisson's ratio  $\nu_a$  and yield stress  $\sigma_{ya}$ ).

### 5.2.2 Operands OMX and OMY

```
OMX = Wxa  
OMY = Wya
```

The steel sections of a bed of reinforcements define given according to the directions  $x$  and  $y$  (in  $m^2/m$  linear, the thickness being then given in  $m$ ).

It is checked that  $Wxa \geq 0$  and  $Wya \geq 0$ .

### 5.2.3 Operands X-ray and RY

```
X-ray = rxa  
RY = rya
```

Define the position adimensionnée of a bed of reinforcements compared to the thickness of the concrete hull, given in the directions  $x$  and  $y$  ( $-1 \leq rxa \leq 1$ ,  $-1 \leq rya \leq 1$ , figure 3).

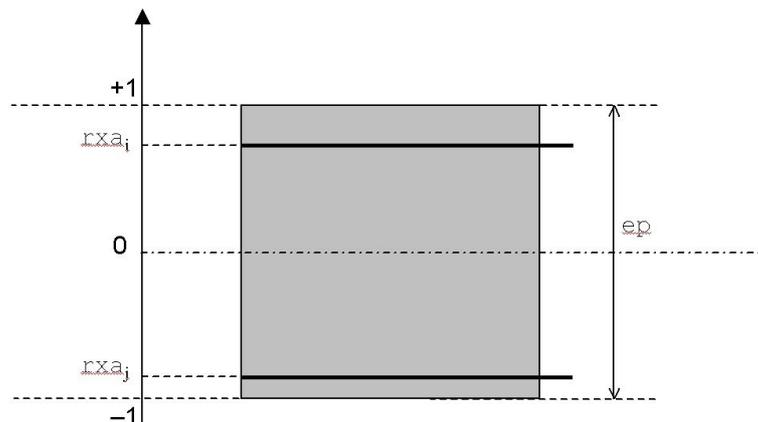


Figure 5.2.3-a: Définition of the adimensionnée position of the beds of reinforcements.

## 5.3 Keyword CABLE\_PREC

The keyword factor `CABLE_PREC` allows to define the geometrical characteristics and material of the cables of prestressed as well as the prestressing force used.

### 5.3.1 Operand MATER

`MATER = mat_cable`

The name of material produced defines by `DEFI_MATERIAU` used for the cables of prestressing. This operand makes it possible to recover the parameters material used for the cables of prestressing (Young modulus  $E_p$ , Poisson's ratio  $\nu_p$  and yield stress  $\sigma_{yp}$ ).

### 5.3.2 Operands OMX and OMY

`OMX = W xp`  
`OMY = W YP`

The steel sections of a bed of cables of prestressing define given according to the directions  $x$  and  $y$  (in  $m^2/m$  linear, the thickness being then given in  $m$ ).

It is checked that  $Wxp \geq 0$  and  $Wyp \geq 0$ .

### 5.3.3 Operands X-ray and RY

`X-ray = rxp`  
`RY = ryp`

Define the adimensionnée position of a bed of cables of prestressing compared to the thickness of the concrete hull, given in the directions  $x$  and  $y$  ( $-1 \leq rxp \leq 1$ ,  $-1 \leq ryp \leq 1$ ).

### 5.3.4 Operands PREX and PREY

`PREX = precx,`  
`PREY = precy,`

The forces of prestressed (in Newton) in the directions define  $x$  and  $y$  (they must be normally negative because one applies a compressive force).

## 5.4 Keyword LINER

The keyword factor LINER allows to define the geometrical characteristics and material of the metal liner.

### 5.4.1 Operand MATER

```
MATER = mat_liner
```

The name of material produced defines by DEFI\_MATERIAU used for the metal liner. This operand makes it possible to recover the parameters material used for the metal liner (Young modulus  $E_l$ , Poisson's ratio  $\nu_l$  and yield stress  $\sigma_{yl}$ ).

### 5.4.2 Operand OML

```
OML = wl
```

The thickness of the liner defines (in meters according to the choice operated for the other dimensioned parameters). It is checked that  $wl \geq 0$ .

### 5.4.3 Operand RLR

```
RLR = rlr,
```

The adimensionnée position of the liner compared to the thickness of the concrete hull defines (in practice,  $rlr = -1$  or  $rlr = 1$ , because the metal liner is laid out opposite lower or higher the concrete hull).

## 5.5 Keyword ALPHA

This keyword makes it possible to define a thermal dilation coefficient "average" (and isotropic) for the element of hull.

## 5.6 Keyword INFORMATION

Impression with the format RESULT list of the homogenized parameters used as starter of the model of behavior GLRC\_DAMAGE.

## 6 Example of use

The following example is resulting from test SDNS106A:

```
CHECHMATE = DEFI_GLRC (RELATION = GLRC_DAMAGE,  
    CONCRETE = _F (  
        MATER = MAT_B,  
        THICK = EP,  
        GAMMA = 0.0,  
        QP1 = 0.15,  
        QP2 = 0.15,  
  
        C1N1 = 87.3E6, C1N2 = 87.3E6, C1N3 = 87.3E6,  
        C2N1 = 87.3E6, C2N2 = 87.3E6, C2N3 = 87.3E6,  
        C1M1 = 14.8E6, C1M2 = 14.8E6, C1M3 = 14.8E6,  
        C2M1 = 14.8E6, C2M2 = 14.8E6, C2M3 = 14.8E6, ),  
  
    TABLECLOTH = (  
        _F (MATER = MAT_A1,  
            OMX = 5.65E-4,  
            OMY = 5.65E-4,  
            X-ray = 0.95,  
            RY = 0.95, ),  
  
        _F (MATER = MAT_A1,  
            OMX = 5.65E-4,  
            OMY = 5.65E-4,  
            X-ray = -0.95,  
            RY = -0.95, ), ),  
  
    LINER = _F (  
        MATER = MAT_A2,  
        OML = 6.E-3,  
        RLR = -1. , ),  
  
    CABLE_PREC = _F (  
        MATER = MAT_A2,  
        OMX = 4.56E-3,  
        OMY = 1.35E-2,  
        X-ray = 0.0,  
        RY = 0.0,  
        PREX = -3.0E6,  
        PREY = -3.0E6, ),  
  
    INFORMATION = 2, );
```

### Note:

In this example, 3 different materials are used: MAT\_B (concrete), MAT\_A1 (passive reinforcements) and MAT\_A2 (liner metal and cables of prestressed). Before defining the parameters of DEFI\_GLRC, it is obligatory to use DEFI\_MATERIAU to inform all the parameters concerning these materials:

```
MAT_B=DEFI_MATERIAU (  
    ELAS = _F (  
        E = 30000.E6,  
        NAKED = 0.2,  
        RHO = 2500.0, ),  
  
    BETON_ECRO_LINE = _F (  

```

```

D_SIGM_EPSI = 0.0,
SYT      = 5E6,
SYC      = -35.E6,)),);

MAT_A1=DEFI_MATERIAU (
    ELAS = _F (
        E      = 2.E11,
        NAKED  = 0.0,)),
    ECRO_LINE = _F (
        D_SIGM_EPSI = 0.0,
        SY      = 3.E9,)),);

MAT_A2=DEFI_MATERIAU (
    ELAS = _F (
        E      = 2.E11,
        NAKED  = 0.3,)),
    ECRO_LINE = _F (
        D_SIGM_EPSI = 0.0,
        SY      = 5.E8,)),);
```

Although formulas of homogenisation used in DEFI\_GLRC exploit only the threshold values SY for ECRO\_LINE and SYT, SYC for BETON\_ECRO\_LINE of DEFI\_MATERIAU, one is obliged to also inform the values D\_SIGM\_EPSI as indicated above, since they are obligatory keywords.