

SSLP103 - Calculation of the coefficients of intensity of constraints K_I and K_{II} for a circular plate fissured in linear elasticity

Summary

It is about a test of breaking process in static linear elasticity for a two-dimensional problem. One considers a fissured circular plate (with a tilted crack of 30 degrees compared to the x-axis) for which one calculates:

- coefficients of intensity of constraints K_I and K_{II} ,
- the rate of refund of energy G starting from the formula of IRWIN.

The interest of the test is to know the analytical solution which gives the coefficients of intensity of constraints and to have a tilted crack.

Two modelings are:

- Modeling a: FEM for elements C_PLAN, D_PLAN
- Modeling b: FEM for elements D_PLAN_INCO_UPG, D_PLAN_INCO_UP


This test understands a modeling which treats successively the plane strains and the plane stresses (elements of continuous mediums).

The digital results do not deviate more 1 % with 2 % values of reference.

1 Problem of reference

1.1 Geometry

It is about a circular plate of ray $OA=100\text{ mm}$, with a tilted crack of 30 degrees compared to the x-axis.

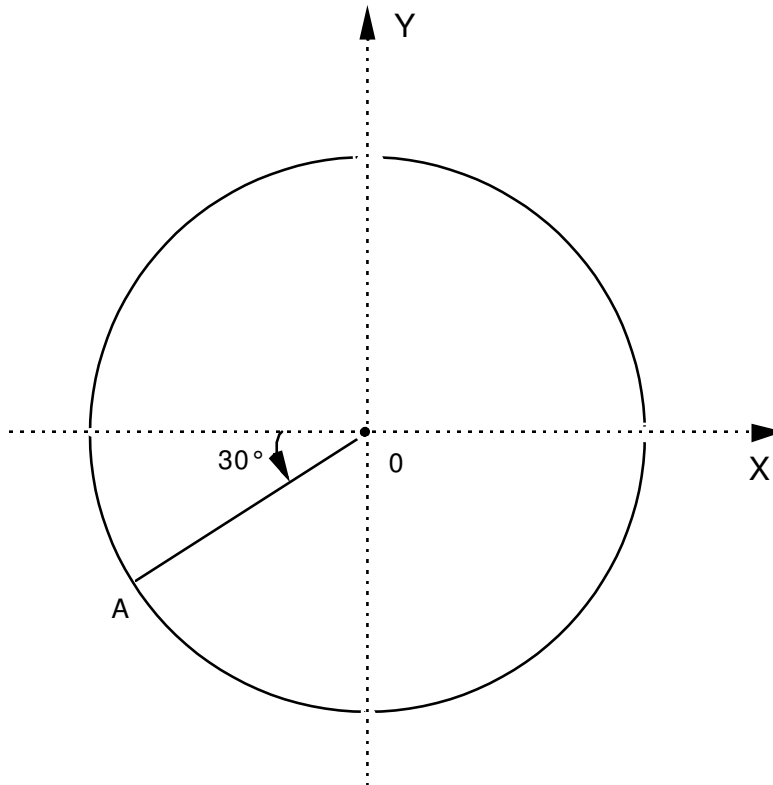

1.2 Material properties

The characteristics of material are the following ones:

$$E = 200\,000\text{ MPa}$$


$$\nu = 0.3$$

1.3 Boundary conditions and loadings

Displacements are imposed on the contour of the plate. They result from the singular analytical solution in mixed mode (with $K_I=2.$ and $K_{II}=1.$).

2 Reference solution

2.1 Method of calculating used for the reference solution

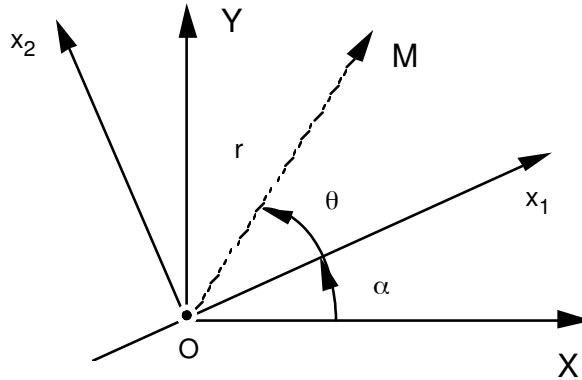

In plane strains or plane stresses, the distribution of displacements is given in this reference mark $(0, x_1, x_2)$ by:

$$\begin{cases} u_1 = \frac{1+\nu}{E} \sqrt{\frac{r}{2\pi}} \left(K_I \cos \frac{\theta}{2} (k - \cos \theta) + K_{II} \sin \left(\frac{\theta}{2} \right) (k - \cos \theta + 2) \right) \\ u_2 = \frac{1+\nu}{E} \sqrt{\frac{r}{2\pi}} \left(K_I \sin \frac{\theta}{2} (k - \cos \theta) - K_{II} \cos \left(\frac{\theta}{2} \right) (k + \cos \theta - 2) \right) \end{cases}$$

with $k = 3 - 4\nu$ in plane deformations

$$k = \frac{3-\nu}{1+\nu} \text{ in plane constraints}$$

or in the reference mark (O, X, Y) by:
$$\begin{cases} u_x = \cos \alpha u_1 - \sin \alpha u_2 \\ u_y = \sin \alpha u_1 + \cos \alpha u_2 \end{cases}$$

On the contour of the plate, one a: $r = OA = 100 \text{ mm}$.

One chooses to take $K_I = 2$. and $K_{II} = 1$. and to impose displacements on the contour of the circular plate.

2.2 Results of reference

$$K_I = 2.$$

$$K_{II} = 1.$$

$$G = 2.275 \cdot 10^{-5} \quad \text{in plane deformations}$$

$$G = 2.5 \cdot 10^{-5} \quad \text{in plane constraints}$$


2.3 Bibliographical references

- 1) H.D. BUI Mécanique of Brittle fracture - ED. Masson 1978

3 Modeling a: FEM for elements D_PLAN and C_PLAN

3.1 Characteristics of modeling

Calculation is carried out in plane constraints (C_PLAN) then in plane deformations (D_PLAN).

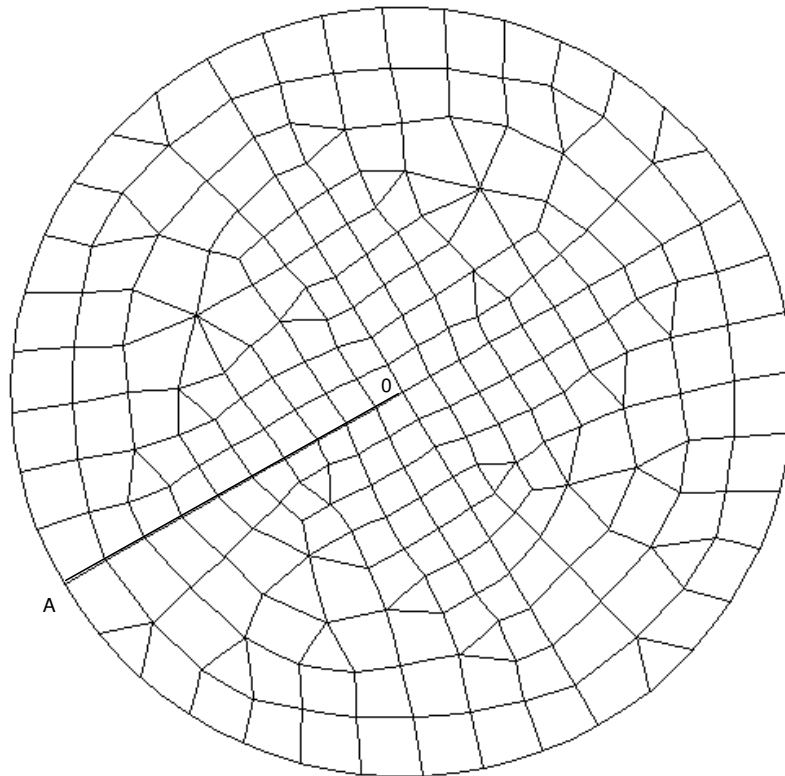

3.2 Characteristics of the grid

Many nodes: 737

Many meshes and types: 204 meshes QUAD8, 30 meshes TRIA6

3.3 Sizes tested and results

The values tested are the coefficients of intensity of constraints K_I and K_{II} and the rate of refund of energy G calculated by the formula of IRWIN:

Identification	Reference	Aster	% difference
Plane constraints			
K_I	2.0	2.0067	0.33
K_{II}	1.0	0.9877	1.23
G	$2.5 \cdot 10^{-5}$	$2.5213 \cdot 10^{-5}$	0.85
Plane deformations			

K_I	2.0	2.0030	0.15
K_{II}	1.0	0.9960	0.39
G	$2,275 \cdot 10^{-5}$	$2.2968 \cdot 10^{-5}$	0.96

3.4 Remarks

The formula of IRWIN gives: $G = \frac{(1-\nu^2)}{E} (K_I^2 + K_{II}^2)$ in plane deformations

and $G = \frac{1}{E} (K_I^2 + K_{II}^2)$ in plane constraints.

Calculations are carried out with a crown of lower integration of ray 10.0 and of higher ray 20.0 .

4 Modeling b: FEM for elements D_PLAN_INCO_UPG, D_PLAN_INCO_UP

4.1 Characteristics of modeling

Identical to modeling A except the use of the elements D_PLAN_INCO_UPG, D_PLAN_INCO_UP.

4.2 Characteristics of the grid

Identical to modeling A

4.3 Sizes tested and results

The values tested are the coefficients of intensity of constraints K_I and K_{II} and the rate of refund of energy G calculated by the formula of IRWIN:

Identification	Method	Reference	Type of reference	% tolerance
G	CALC_G	2.275E-5	ANALYTICAL	2
K_I	CALC_K_G	2	ANALYTICAL	2
K_{II}	CALC_K_G	1	ANALYTICAL	7
G	CALC_K_G	2.275E-5	ANALYTICAL	2
G_{IRWIN}	CALC_K_G	2.275E-5	ANALYTICAL	3

5 Summaries of the results

The digital values of the coefficients of intensity of constraints and the rate of refund of energy do not deviate more than 1 with 2% values of reference, which is satisfactory.

The grid could be improved, in particular in the vicinity of the bottom of crack.