

## SSLV135 – Criteria of starting in fatigue under multiaxial loadings for a structure

---

### Summary:

This CAS-test aims to test the operator `CALC_FATIGUE` who calculates the damage for all the points of structure.


The geometry treated here is a cube without defect with which one carries out a linear elastic mechanical calculation followed by the calculation of the critical plan of shearing in each point of Gauss and each node.

- modeling a: criteria `MATAKE_MODI_AC`, `DANG_VAN_MODI_AC`, `VMIS_TRESCA`, criterion in formula, periodic and biaxial loading proportional;
- modeling b: criterion `MATAKE_MODI_AV`, `DANG_VAN_MODI_AV`, `FATESOCI_MODI_AV`, criterion in formula, loading not-periodical and biaxial proportional ;
- modeling C: criteria `MATAKE_MODI_AC` and `DANG_VAN_MODI_AV`, criterion in formula, loading multiaxial, non-proportional;
- modeling D : criterion in formulaE, to test new sizes, tankgemmate uniaxial elastoplastic and periodic.
- modeling E : criterion in formulaE, to test new sizes (in constraints) , tankgemmate biaxial elastoplastic and not-periodical.
- modeling F : criterion in formulaE, to test new sizes (in deformations) , tankgemmate biaxial rubber band with variable amplitude and tankgemmate uniaxial elastoplastic and not-periodical.
- modeling G: criteria `MATAKE_MODI_AC`, `DANG_VAN_MODI_AC`, `MATAKE_MODI_AV`, `DANG_VAN_MODI_AV`, `FATESOCI_MODI_AV`. One tests the change of the direction of the critical plan on which the damage or shearing is maximum.
- modeling H: criteria in formula of the standard plan criticizes with the keyword `FORMULE_CRITIQUE`

The criteria in modeling A are said “to plan of critical shearing”, they are adapted to the periodic loadings. The criteria in modeling B can be qualified criteria “with plan of critical damage”, they can be used when the loading is not periodical. The criterion `VMIS_TRESCA` is not a criterion of tiredness, it determines the variation of maximum amplitude of the tensor of the constraints. The criteria formulates some making it possible to the user to build criteria according to the predefined sizes are also tested. The criteria in modeling H are said “to plan criticizes general”, they are adapted to the periodic loadings.

## 1 Problem of reference

### 1.1 Geometry

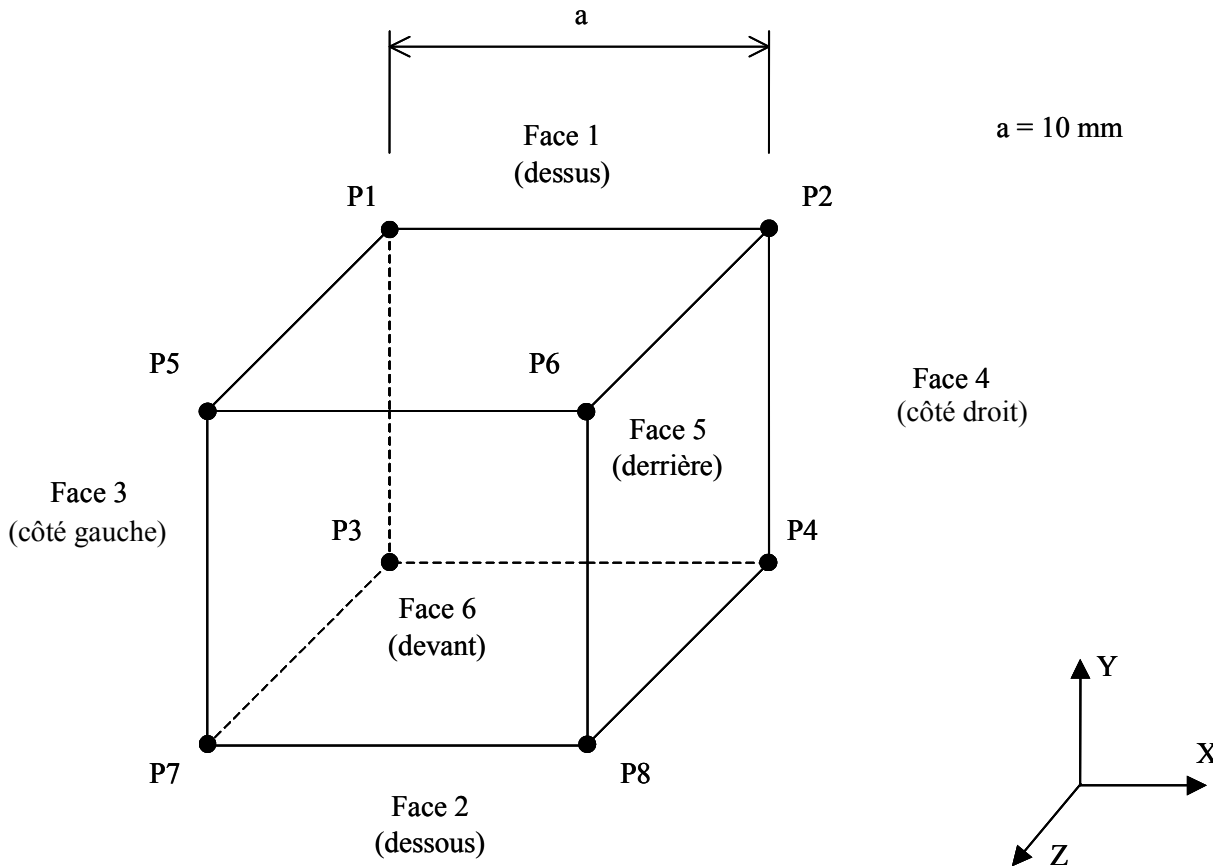

The cube has  $10 \text{ mm}$  on side.

### 1.2 Material properties

#### 1.2.1 Modelings: With, B, C and F

Young modulus:  $E = 200000 \text{ MPa}$

Poisson's ratio:  $\nu = 0.3$

#### 1.2.2 Modelings D and H

modulus Young and the Poisson's ratio is identical to those of other modelings.

Yield stress of material:  $\sigma_o = 150.0 \text{ MPa}$

The elastoplastic behavior of Von Mises with linear isotropic work hardening with the slope of curve of work hardening:  $H = 50000.0 \text{ MPa}$

#### 1.2.3 Modeling E

modulus Young and the Poisson's ratio is identical to those of other modelings.

Yield stress of material:  $\sigma_o = 900.0 \text{ MPa}$

The elastoplastic behavior of Von Mises with linear isotropic work hardening with the slope of curve of work hardening:  $H=50000.0 \text{ MPa}$

## 1.2.4 Modeling F

In this modeling, two different materials are considered. First is similar to paragraph 1.2.1 (i.e. purely elastic), and second is similar to material used in modeling E (1.2.3).

## 1.2.5 Modeling G

In this modeling, two different materials are considered.

The first material is elastic with the Young modulus:  $E=193000 \text{ MPa}$  and the Poisson's ratio:  $\nu=0,3$

The second material is elastoplastic, the modulus Young and the Poisson's ratio is identical to first material.

Yield stress of material:  $\sigma_o=208.0 \text{ MPa}$ . The elastoplastic behavior of Von Mises with linear isotropic work hardening with the slope of curve of work hardening:  $H=50000.0 \text{ MPa}$

## 1.3 Curves of Wöhler and Manson-Whetstone sheath

Modelings use all the curves of Wöhler (i.e. a curve in constraint) and of Manson-Whetstone sheath (i.e. a curve in deformation).

Here the curve of Wöhler (alternate traction and compression controlled in constraint):

Half amplitude of constraint ( $\text{MPa}$ )	138.0	152.0	165.0	180.0	200.0	250.0	295.0
Many cycles	1.0E+6	5.0E+5	2.0E+5	1.0E+5	5.0E+4	2.0E+4	1.2E+4
Half amplitude of constraint ( $\text{MPa}$ )	305.0	340.0	430.0	540.0	690.0	930.0	1210.0
Many cycles	1.0E+4	5.0E+3	2.0E+3	1.0E+3	5.0E+2	2.0E+2	1.0E+2
Half amplitude of constraint ( $\text{MPa}$ )	1590.0	2210.0	2900.0				
Many cycles	5.0E+1	2.0E+1	1.0E+1				

Table 1.3-1: Curve of Wöhler

Here the curve of Manson-Whetstone sheath (alternate traction and compression controlled in deformation):

Deformation	0.00226	0.0023	0.0025	0.0027	0,003	0.0035
Many cycles	5.8E+6	4.6E+6	2.39284E+5	1.49535E+5	7.3544E+4	3.3821E+4
Deformation	0,006	0.0085	0,010	1,000		
Many cycles	2.85E+3	1.068E+3	5.62E+2	1.0		

Table 1.3-2: Curve of Manson-Whetstone sheath


## 1.4 Boundary conditions and loadings

### 1.4.1 Modelings: WITH, B

- Displacements according to the axis  $X$  face 3 are blocked ( $DX=0.0$ ).
- Displacements according to the axis  $Y$  face 2 are blocked ( $DY=0.0$ ).
- Displacements of the point  $P3$  are blocked according to the axis  $Z$  ( $DZ=0.0$ ).
- We apply an alternate biaxial loading (traction and compression) according to the axes  $X$  and  $Y$ .  
 $F_x(t)$  represent the alternate efforts applied to face 4 according to the axis  $X$  and  $F_y(t)$  represent the alternate efforts applied to the face 1 according to the axis  $Y$ .

Warning : The translation process used on this website is a "Machine Translation". It may be imprecise and inaccurate in whole or in part and is provided as a convenience.


Loading for these modelings:

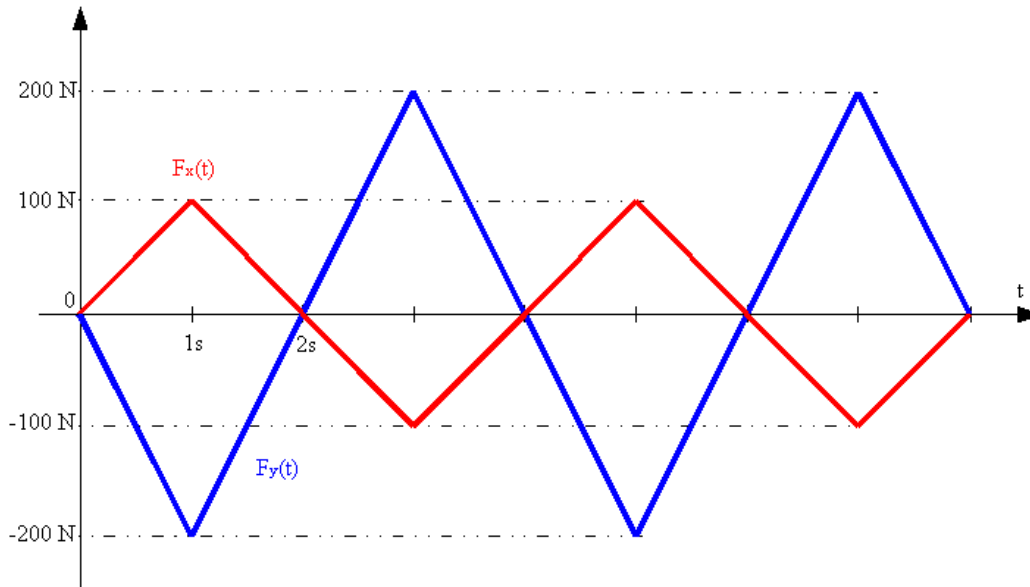

## 1.4.2 Modeling C

- Displacements according to the axis  $X$  face 3 are blocked ( $DX=0.0$ ).
- Displacements according to the axis  $Y$  face 3 are blocked ( $DY=0.0$ ).
- Displacements according to the axis  $Z$  face 2 are blocked ( $DZ=0.0$ ).
- We apply a multiaxial loading: traction and compression according to the axis  $X$ , shearing according to the axes  $Y$  and  $Z$ .  $F_x(t)$  represent the efforts applied to face 4 according to the axis  $X$ ,  $F_y(t)$  represent the efforts applied to face 4 according to the axis  $Y$  and  $F_z(t)$  represent the efforts applied to face 1 according to the axis  $Z$ .

Loading for this modeling:

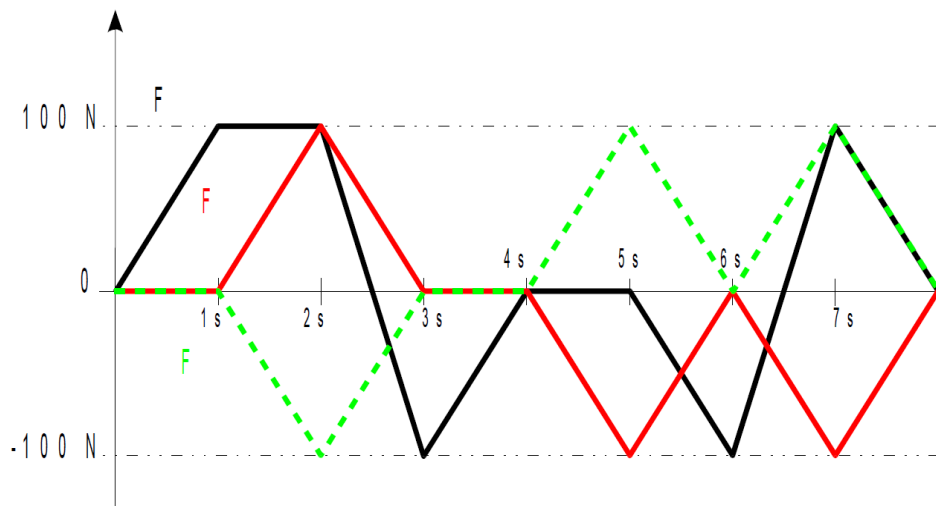

## 1.4.3 Modelings D and H

- Displacements according to the axis  $X$  face 3 are blocked ( $DX=0.0$ ).
- Displacements according to the axis  $Y$  face 3 are blocked ( $DY=0.0$ ).
- Displacements according to the axis  $Z$  face 2 are blocked ( $DZ=0.0$ ).
- In this modeling, we apply a periodic uniaxial loading.


$t$	0	1	2	3	4	5	6
$F_x(t)$	0	200	0	-200	0	200	0

It is noted that this history of loading involves a plastic deformation in calculation. It is also noted that the monotonous history of loading enters  $t=0$  and  $t=1$  (the part of the monotonous loading) is not taken into account in the fatigue analysis.

## 1.4.4 Modeling E

- Displacements blocked here are the same ones as in modeling O
- We apply a biaxial loading here not-periodical.

$t$	0	1	2	2,75	3,5
$F_x(t)$	0	1200	0	900	0
$F_y(t)$	0	-800	0	-600	0

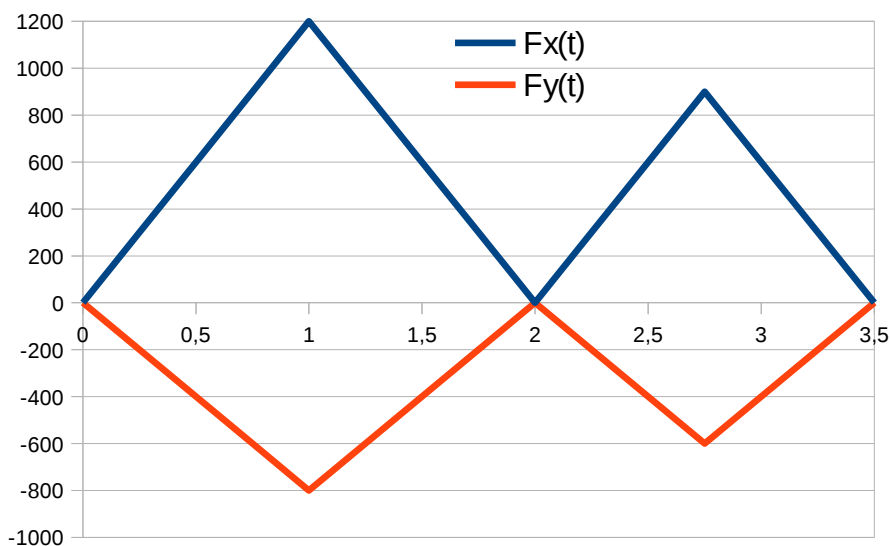


## 1.4.5 Modeling F

- Displacements blocked here are the same ones as in modeling O
- In this modeling, we apply three distinct loadings. First is biaxial, the two others are uniaxial.

**First loading** (association of  $TR\_CS$  and of  $COEFF$  in the command file):

$t$	0	1	2	2,75	3,5
-----	---	---	---	------	-----

$F_x(t)$	0	1200	0	900	0
$F_y(t)$	0	-600	0	-450	0

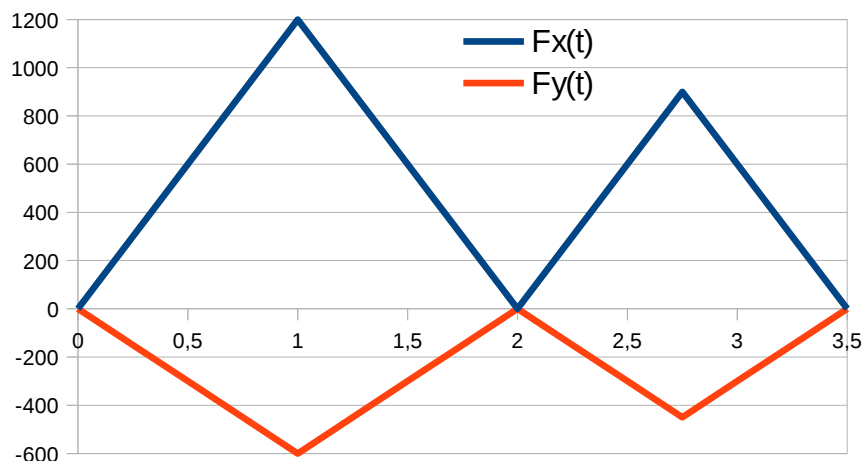

**Second loading** (association of TR\_CS2 and of COEF2 in the command file):


$t$	0	1	2.5625	3.5625	5.5625
$F_x(t)$	0	1200	-675	900	-675

**Third loading** (association of TR\_CS2 and of COEF3 in the command file):

$t$	0	1	2	3	4
$F_x(t)$	0	1800	-600	2400	-1200

## 1.4.6 Modeling G

- Displacements blocked here are the same ones as in modeling A
- We apply an alternate biaxial loading (traction and compression) according to the axes  $X$  and  $Y$ .  $\sigma_x$  represent the alternate efforts applied to face 4 according to the axis  $X$  and  $\sigma_y$  represent the alternate efforts applied to the face 1 according to the axis  $Y$ .
- To study effects of the average constraint on the orientation of the critical plan, only of the loadings biaxial, proportional according to directions of  $X$  and  $Y$  are considered.

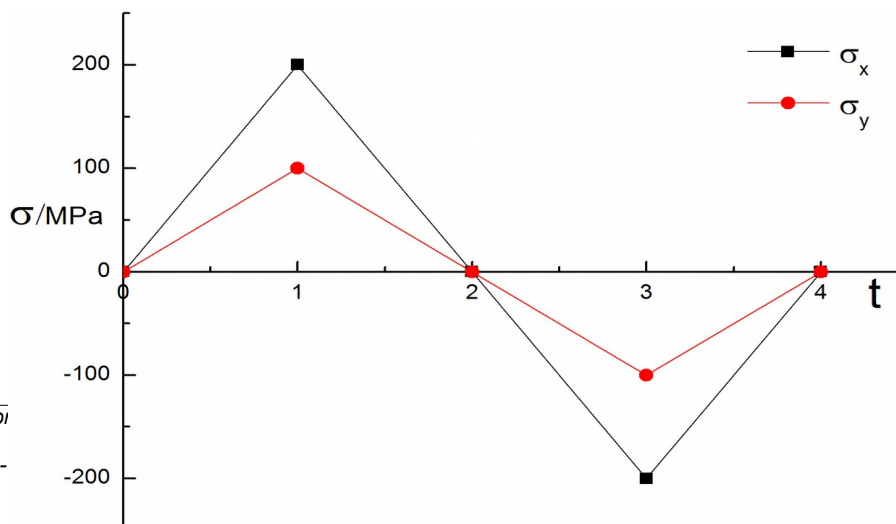

- Two parameters are defined

$$\lambda = \frac{\sigma_{y,a}}{\sigma_{x,a}}$$
$$\alpha = \frac{\sigma_{y,m}}{\sigma_{y,a}} = \frac{\sigma_{x,m}}{\sigma_{x,a}}$$

where  $\sigma_{x,a}$  ,  $\sigma_{y,a}$  amplitudes of the constraints represent according to  $X$  and  $Y$  , respectively.  $\sigma_{x,m}$  and  $\sigma_{y,m}$  the values of the average constraints represent according to  $X$  and  $Y$  directions, respectively. One takes  $\sigma_{x,a} = 200 \text{ MPa}$  ,  $\lambda = 1$  and  $\alpha$  vary from -1 to 10 with an interval of 0.5.

## 1.5 Initial conditions

Without object for a static analysis.

## 2 Reference solution

### 2.1 Method of calculating used for the reference solution

In the case of an alternate biaxial loading where the pressures applied are such as:  $\sigma_x = \lambda \sigma_y$ , with  $|\lambda| > 1$  and  $\lambda < 0$ , it is shown [bib1] that the half amplitude of maximum shearing  $\Delta \tau / 2 = (\Delta \sigma_x + \Delta \sigma_y) / 4$ , where  $\Delta \sigma_x / 2$  and  $\Delta \sigma_y / 2$  the half amplitudes of pressures applied according to the axes represent  $x$  and  $y$ . Moreover, there are two critical plans in which shearing is maximum:

### 2.2 Results of reference for modeling A

See the references [bib1] and [R7.04.04].

Half amplitude of maximum shearing:

$N_1$	$N_2$
$\Delta \sigma_x / 2$ ( MPa )	$\Delta \sigma_y / 2$ ( MPa )
100	200
	$\Delta \tau / 2$ ( MPa )
	150

**Note:**

| The half amplitude of maximum shearing is identical for the two critical plans.

**Normal vectors with the two critical plans:**

	$n_1$	$n_2$
Component $x$	$-1/\sqrt{2}$	$1/\sqrt{2}$
Component $y$	$1/\sqrt{2}$	$1/\sqrt{2}$
Component $z$	0	0

**Normal maximum constraints in the fields of the normals  $n_1$  and  $n_2$  :**

$$N_{\max}(n_1) = 50 \text{ MPa} \text{ and } N_{\max}(n_2) = 50 \text{ MPa} .$$



**Hydrostatic pressure maximum, independent with respect to the plans of normals  $n_1$  and  $n_2$  :**

$$P=33.33333 \text{ MPa} .$$

**Normal average constraints in the fields of the normals  $n_1$  and  $n_2$  :**

$$N_m(n_1)=0 \text{ MPa} \text{ and } N_m(n_2)=0 \text{ MPa} .$$

**Normal maximum deformations in the fields of the normals  $n_1$  and  $n_2$  :**

$$\varepsilon_{\max}(n_1)=1.75 \cdot 10^{-4} \text{ and } \varepsilon_{\max}(n_2)=1.75 \cdot 10^{-4}$$

**Normal average deformations in the fields of the normals  $n_1$  and  $n_2$  :**

$$\varepsilon_m(n_1)=0 \text{ and } \varepsilon_m(n_2)=0 .$$

**Criterion MATAKE\_MODI\_AC**

$$\frac{\Delta \tau(n_i)}{2} + a N_{\max}(n_i) \leq b, \quad i=1, 2$$

where  $a=1$  and  $b=2$  .

**Equivalent constraints within the meaning of MATAKE in the fields of the normals  $n_1$  and  $n_2$  :**

$$\sigma_{eq}(n_i) = \left( \frac{\Delta \tau(n_i)}{2} + a N_{\max}(n_i) \right) \frac{f}{t}, \quad i=1, 2$$

where  $f$  and  $t$  represent, respectively, the limit of endurance in alternating bending and the limit of endurance in alternate torsion. Here  $f/t$  is equal to 1,5 . Consequently we have:

$$\sigma_{eq}(n_1)=300 \text{ MPa} \text{ and } \sigma_{eq}(n_2)=300 \text{ MPa} .$$

**Many cycles to the rupture in the fields of the normals  $n_1$  and  $n_2$  :**

Starting from the curve of Wöhler, cf [Table 1.2-1], and from the equivalent constraints within the meaning of MATAKE, we obtain:

$$Nb_{cr}(n_1)=Nb_{cr}(n_2)=10946 \text{ cycles} .$$

**Damage in the fields of the normals  $n_1$  and  $n_2$  :**

$$ENDO(n_1)=ENDO(n_2)=9.13565 \cdot 10^{-5} .$$

Criterion of Dang Van adapted to the periodic loadings : DANG\_VAN\_MODI\_AC

$$\frac{\Delta \tau(n_i)}{2} + a P \leq b, \quad i=1, 2$$

where  $a=1$  and  $b=2$  .

Equivalent constraints within the meaning of DANG VAN in the fields of the normals  $n_1$  and  $n_2$  :

$$\sigma_{eq}(n_i) = \left( \frac{\Delta \tau(n_i)}{2} + a P \right) \frac{c}{t}, \quad i=1, 2$$

where  $c$  and  $t$  represent, respectively, the limit of endurance in alternate shearing and the limit of endurance in alternate traction and compression. Here  $c/t$  is equal to 1,5 . Consequently we have:

$$\sigma_{eq}(n_1) = 275 \text{ MPa} \quad \text{and} \quad \sigma_{eq}(n_2) = 275 \text{ MPa} .$$

Many cycles to the rupture in the fields of the normals  $n_1$  and  $n_2$

Starting from the curve of Wöhler, cf [Table 1.2-1], and from the equivalent constraints within the meaning of DANG VAN, we obtain:

$$Nb_{cr}(n_1) = Nb_{cr}(n_2) = 14903 \text{ cycles} .$$

Damage in the fields of the normals  $n_1$  and  $n_2$  :

$$ENDO(n_1) = ENDO(n_2) = 6.709959 \cdot 10^{-5} .$$

For the option `COURBE_GRD_VIE = 'FORMES_VIE'` and `FORMULE_VIE = WHOL_F` where the curve of life is provided by a formula, the results of reference are identical to those called with the names except those of `NBRUPT` and `ENDO` as one uses a curve of different life.

- the curve `WHOL_F` of formula ( $\text{grandeur\_équivalente} = 4098.3 \times (NBRUP^{-0.2693})$ ) is initially provided by a function tabulée to calculate values of reference of `NBRUPT` and `ENDO`.
- the curve `MANCO2` of formula ( $\text{grandeur\_équivalente} = 0.2 \times (NBRUP^{-0.1619})$ ) is initially provided by a function tabulée to calculate values of reference of `NBRUPT` and `ENDO`.

## 2.3 Results of reference for modeling B

Criterion of MATAKE adapted to the nonperiodic loadings: `MATAKE_MODI_AV`

For this criterion there are no analytical results.

Criterion of Dang Van adapted to the nonperiodic loadings: `DANG_VAN_MODI_AV`

For this criterion there are no analytical results.

See the references [bib2] and [R7.04.04].

**Half amplitude of constraint:**

$$\frac{\Delta \sigma_x / 2 \text{ (MPa)}}{100} \quad \frac{\Delta \sigma_y / 2 \text{ (MPa)}}{200}$$

Criterion of FATEMI and SOCIE adapted to the nonperiodic loadings: `FATESOCI_MODI_AV`

For this criterion there are no analytical results.

See the references [bib3] and [R7.04.04].

**Half amplitude of constraint:**

$$\frac{\Delta \sigma_x / 2 \text{ (MPa)}}{100} \quad \frac{\Delta \sigma_y / 2 \text{ (MPa)}}{200}$$



Criterion of Von Mises and TRESCA applied in search of the maximum variation of a tensor of constraint. The loading can be periodic or not: VMIS\_TRESCA

See the reference [R7.04.04].

**Half amplitude of constraint:**

$$\frac{\Delta \sigma_x / 2 \text{ (MPa)}}{100} \quad \frac{\Delta \sigma_y / 2 \text{ (MPa)}}{200}$$

**Criterion of Von Mises:**

Within the space of constraints with six dimensions:

$$\sigma_s = \sqrt{\frac{1}{2} \left[ (\sigma_{xx} - \sigma_{yy})^2 + (\sigma_{yy} - \sigma_{zz})^2 + (\sigma_{zz} - \sigma_{xx})^2 + 6(\sigma_{xy}^2 + \sigma_{xz}^2 + \sigma_{yz}^2) \right]}$$

with  $\sigma_{xx} = 200 \text{ MPa}$ ,  $\sigma_{yy} = -400 \text{ MPa}$  and  $\sigma_{zz} = \sigma_{xy} = \sigma_{xz} = \sigma_{yz} = 0$ , one obtains:

$$\frac{\sigma_s \text{ (MPa)}}{529.15026221292}$$

**Criterion of Tresca:**

Within the space of principal constraints with three dimensions:

$$\sigma_s = \text{Sup}_{i \neq j} (|\sigma_i - \sigma_j|),$$

with  $\sigma_{xx} = 200 \text{ MPa}$ ,  $\sigma_{yy} = -400 \text{ MPa}$  and  $\sigma_{zz} = \sigma_{xy} = \sigma_{xz} = \sigma_{yz} = 0$ , one obtains:

$$\frac{\sigma_s \text{ (MPa)}}{600}$$

## 2.4 Results of reference for modeling C

There is no result of reference for modeling G. This modeling has as single objective to test the routines cer3pt.f and raxini.f.

## 2.5 Results of reference for modeling D

One starts with a calculation of the constraint, the total deflection and the plastic deformation with the order CALC\_CHAMP. The results are listed in the following Table by knowing that the other components are equal to zero.

The results are got with the node NI.

t	$\sigma_{xx}$	$\epsilon_{xx}^{tot}$	$\epsilon_{yy}^{tot}$	$\epsilon_{zz}^{tot}$	$\epsilon_{xx}^p$	$\epsilon_{yy}^p$	$\epsilon_{zz}^p$
0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00
2.50E-01	5.00E+01	2.50E-04	-7.50E-05	-7.50E-05	-1.48E-20	-7.40E-20	-5.98E-20
5.00E-01	1.00E+02	5.00E-04	-1.50E-04	-1.50E-04	-4.57E-19	2.71E-19	2.84E-20
7.50E-01	1.50E+02	7.50E-04	-2.25E-04	-2.25E-04	-2.29E-19	2.15E-19	-2.71E-20
1.00E+00	2.00E+02	1.75E-03	-6.75E-04	-6.75E-04	7.50E-04	-3.75E-04	-3.75E-04

Warning : The translation process used on this website is a "Machine Translation". It may be imprecise and inaccurate in whole or in part and is provided as a convenience.

Copyright 2017 EDF R&D - Licensed under the terms of the GNU FDL (<http://www.gnu.org/copyleft/fdl.html>)

1.25E+00	1.50E+02	1.50E-03	-6.00E-04	-6.00E-04	7.50E-04	-3.75E-04	-3.75E-04
1.50E+00	1.00E+02	1.25E-03	-5.25E-04	-5.25E-04	7.50E-04	-3.75E-04	-3.75E-04
1.75E+00	5.00E+01	1.00E-03	-4.50E-04	-4.50E-04	7.50E-04	-3.75E-04	-3.75E-04
2.00E+00	1.98E-08	7.50E-04	-3.75E-04	-3.75E-04	7.50E-04	-3.75E-04	-3.75E-04
2.25E+00	-5.00E+01	5.00E-04	-3.00E-04	-3.00E-04	7.50E-04	-3.75E-04	-3.75E-04
2.50E+00	-1.00E+02	2.50E-04	-2.25E-04	-2.25E-04	7.50E-04	-3.75E-04	-3.75E-04
2.75E+00	-1.50E+02	-7.50E-04	2.25E-04	2.25E-04	-7.14E-13	7.02E-13	1.17E-14
3.00E+00	-2.00E+02	-1.75E-03	6.75E-04	6.75E-04	-7.50E-04	3.75E-04	3.75E-04
3.25E+00	-1.50E+02	-1.50E-03	6.00E-04	6.00E-04	-7.50E-04	3.75E-04	3.75E-04
3.50E+00	-1.00E+02	-1.25E-03	5.25E-04	5.25E-04	-7.50E-04	3.75E-04	3.75E-04
3.75E+00	-5.00E+01	-1.00E-03	4.50E-04	4.50E-04	-7.50E-04	3.75E-04	3.75E-04
4.00E+00	3.26E-09	-7.50E-04	3.75E-04	3.75E-04	-7.50E-04	3.75E-04	3.75E-04
4.25E+00	5.00E+01	-5.00E-04	3.00E-04	3.00E-04	-7.50E-04	3.75E-04	3.75E-04
4.50E+00	1.00E+02	-2.50E-04	2.25E-04	2.25E-04	-7.50E-04	3.75E-04	3.75E-04
4.75E+00	1.50E+02	7.50E-04	-2.25E-04	-2.25E-04	6.51E-12	-2.64E-12	-3.87E-12
5.00E+00	2.00E+02	1.75E-03	-6.75E-04	-6.75E-04	7.50E-04	-3.75E-04	-3.75E-04

Let us define certain sizes first of all:

- the diverter of the tensor of the constraints:  $s = \sigma - \frac{1}{3} tr(\sigma) \cdot I$  where  $I$  is the matrix identity
- the diverter of the tensor of the deformations:  $e = \epsilon - \frac{1}{3} tr(\epsilon) \cdot I$  where  $I$  is the matrix identity

It is stressed that the results in interval of time between 0 and 1 second are for the monotonous part of the loading and are not taken into account in the calculation of the sizes for the cyclic behavior.

Then, here reference solutions for:

'DEPSPE' : half-havemplitude of the equivalent plastic deformation:

$$\frac{\Delta \epsilon_{eq}^p}{2} = \frac{1}{2} \max_{t_1} \max_{t_2} \sqrt{\frac{2}{3} (\epsilon^p(t_1) - \epsilon^p(t_2)) : (\epsilon^p(t_1) - \epsilon^p(t_2))} = 7.5E-4$$

'EPSPR1' : half-amplitude of the première principal deformation (with the taking into account of the sign):

$$\frac{\epsilon_{max}^1 - \epsilon_{min}^1}{2} = 7.625E-04$$

'SIGNM1' : maximum normal constraint as regards the principal deformation:

$$\max_t (\sigma(t) \cdot n_1(t) \cdot n_1(t)) = 200 MPa$$

'APHYDR' : half amplitude of the hydrostatic pressure ( $P_a$ )

$$P_a = \frac{P_{max} - P_{min}}{2} = 66.6666 MPa$$

'DENDIS' : density of dissipated energy:

$$W_{cy} = \int_{cycle} \sigma : \dot{\epsilon}^p dt = 0.45$$

'DENDIE' : density of energy of the elastic distortions:

$$W_e = \int_{cycle} \langle s : \dot{e}^e \rangle dt = 0.173333$$

'DSIGEQ' : halfamplitude of the equivalent constraint:

$$\frac{\Delta \sigma_{eq}}{2} = \frac{1}{2} \max_{i1} \max_{i2} \sqrt{\frac{3}{2} (s(t_1) - s(t_2)) : (s(t_1) - s(t_2))} = 200 \text{ MPa}$$

'SIGPR1' : halfamplitude of the first principal constraint (with the taking into account of the sign):

$$\frac{\sigma_{max}^1 - \sigma_{min}^1}{2} = 100 \text{ MPa}$$

'EPSNM1' : maximum normal deformation as regards the principal constraint:

$$\max_t (\boldsymbol{\epsilon}(t) \cdot \mathbf{n}_1(t) \cdot \mathbf{n}_1(t)) = 1.75\text{E}-3$$

'INVA2S' : half-amplitude of second invariant of the deformation:

$$J_2(\Delta \boldsymbol{\epsilon}) = \frac{1}{2} \max_{i1} \max_{i2} \sqrt{\frac{2}{3} (\mathbf{e}(t_1) - \mathbf{e}(t_2)) : (\mathbf{e}(t_1) - \mathbf{e}(t_2))} = 1.616666\text{E}-3$$

'DSITRE' : halfamplitude of the Tresca half-constraint:

$$\frac{\sigma_{max}^{Tresca} - \sigma_{min}^{Tresca}}{4} = 50 \text{ MPa}$$

'DEPTRE' : halfamplitude of the Tresca half-deformation:

$$\frac{\epsilon_{max}^{Tresca} - \epsilon_{min}^{Tresca}}{4} = 6.0625\text{E}-4$$

'EPSPAC' : plastic deformation accumulated:

$$p = 3.67423\text{E}-3$$

'DEPSEE' : half-amplitude of the equivalent elastic strain:

$$\frac{\Delta \epsilon_{eq}^p}{2} = \frac{1}{2} \max_{i1} \max_{i2} \sqrt{\frac{2}{3} (\boldsymbol{\epsilon}^e(t_1) - \boldsymbol{\epsilon}^e(t_2)) : (\boldsymbol{\epsilon}^e(t_1) - \boldsymbol{\epsilon}^e(t_2))} = 0.000866666666$$

## 2.6 Results of reference for modeling E

The results are got with the node *NI*.

<i>t</i>	$\sigma_{xx}$	$\sigma_{yy}$	$\epsilon_{xx}^{tot}$	$\epsilon_{yy}^{tot}$	$\epsilon_{zz}^{tot}$	$\epsilon_{xx}^p$	$\epsilon_{yy}^p$	$\epsilon_{zz}^p$
0.00E+0	0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00
2.50E-1	3.00E+02	-2.00E+02	1.80E-03	-1.45E-03	-1.50E-04	-6.73E-19	-2.69E-18	2.84E-19
5.00E-1	6.00E+02	-4.00E+02	3.60E-03	-2.90E-03	-3.00E-04	-4.71E-19	-4.39E-18	2.61E-19
7.50E-1	9.00E+02	-6.00E+02	1.10E-02	-9.26E-03	-1.15E-03	5.61E-03	-4.91E-03	-7.01E-04
1.00E+0	1.20E+03	-8.00E+02	1.88E-02	-1.60E-02	-2.05E-03	1.16E-02	-1.02E-02	-1.45E-03
1.25E+0	9.00E+02	-6.00E+02	1.70E-02	-1.45E-02	-1.90E-03	1.16E-02	-1.02E-02	-1.45E-03
1.50E+0	6.00E+02	-4.00E+02	1.52E-02	-1.31E-02	-1.75E-03	1.16E-02	-1.02E-02	03
1.75E+0	3.00E+02	-2.00E+02	1.34E-02	-1.16E-02	-1.60E-03	1.16E-02	-1.02E-02	-1.45E-03
2.00E+0	2.30E-13	-3.07E-13	1.16E-02	-1.02E-02	-1.45E-03	1.16E-02	-1.02E-02	03
2.25E+0	3.00E+02	-2.00E+02	1.34E-02	-1.16E-02	-1.60E-03	1.16E-02	-1.02E-02	-1.45E-03
2.50E+0	6.00E+02	-4.00E+02	1.52E-02	-1.31E-02	-1.75E-03	1.16E-02	-1.02E-02	03
2.75E+0	9.00E+02	-6.00E+02	1.70E-02	-1.45E-02	-1.90E-03	1.16E-02	-1.02E-02	-1.45E-03
3.00E+0	6.00E+02	-4.00E+02	1.52E-02	-1.31E-02	-1.75E-03	1.16E-02	-1.02E-02	03
3.25E+0	3.00E+02	-2.00E+02	1.34E-02	-1.16E-02	-1.60E-03	1.16E-02	-1.02E-02	-1.45E-03
3.50E+0	-4.35E-14	-8.66E-13	1.16E-02	-1.02E-02	-1.45E-03	1.16E-02	-1.02E-02	03

									- 1.4 5th-03
									- 1.4 5th-03
									- 1.4 5th-03
									- 1.4 5th-03
									- 1.4 5th-03

It is stressed that the results in interval of time between 0 and 1 second are for the monotonous part of the loading and are not taken into account in the calculation of the sizes for the cyclic behavior.

For the reference solutions we calculated the damage (via ENDO1) with the various sizes available for a nonperiodic loading:

'SIPR1\_1': first principal constraint of the first top of under cycle ( $\sigma_1(1)$ ) and

'SIPR1\_2': first principal constraint of the second top of under cycle ( $\sigma_1(2)$ ):

One uses the half-amplitude of the constraint of the top of the first cycle, namely 600 MPa and the half-amplitude of the constraint of the top of the second cycle, namely 450 Mpa then one adds the damages associated with these two amplitudes.

One evaluates the criterion here following:  $\frac{|SIPR1 - SIPR2|}{2}$

- with the formula of Basquin: grandeur équivalente =  $4098.3 \times (NBRUP)^{-0.2693}$   
one finds  $NBRUP1 = 1255$  and for the damage:  $D1 = 7.968963E - 04$  then  $NBRUP2 = 3652$  and for the damage:  $D2 = 2.738186E - 04$  that is to say a total damage equal to:  
 $D = 1.0707149E - 03$
- with an interpolation of the curve of Wöhler:  
one finds  $NBRUP1 = 742$  and for the damage:  $D = 1.347073E - 03$ . One finds  $NBRUP2 = 1742$  and for the damage:  $D = 5.741842E - 04$  that is to say a total damage equal to:  
 $D = 1.9212575E - 03$

'IFTN1\_1': normal constraint on the level associated with  $\epsilon_1^{tot}(1)$  first top of the under-cycle and

'IFTN1\_2': normal constraint on the level associated with  $\epsilon_1^{tot}(2)$  second top of the under-cycle:

One uses the half-amplitude of the associated constraint  $\epsilon_1^{tot}(1)$ , namely 600 MPa and the half-amplitude of the associated constraint  $\epsilon_1^{tot}(2)$ , namely 450 MPa then one adds the damages associated with these two amplitudes.

One evaluates the criterion here following:  $\frac{|SITN1 - SITN2|}{2}$

- with the formula of Basquin: grandeur équivalente =  $4098.3 \times (NBRUP)^{-0.2693}$   
one finds  $NBRUP1 = 1255$  and for the damage:  $D1 = 7.968963E - 04$  then  $NBRUP2 = 3652$  and for the damage:  $D2 = 2.738186E - 04$  that is to say a total damage equal to:  
 $D = 1.0707149E - 03$
- with an interpolation of the curve of Wöhler:

one finds  $NBRUP1=742$  and for the damage:  $D=1.347073E-03$  one finds  $NBRUP2=1742$  and for the damage:  $D=5.741842E-04$  that is to say a total damage equal to:  
 $D=1.9212575E-03$

'IFPNR1\_1': normal constraint on the level associated with  $\epsilon_1^p(1)$  first top of the under-cycle and  
'IFPNR1\_2': normal constraint on the level associated with  $\epsilon_1^p(2)$  second top of the under-cycle:

One uses the value the half-amplitude of the associated constraint  $\epsilon_1^p(1)$ , namely  $600\text{ Mpa}$  has and the half-amplitude of the associated constraint  $\epsilon_1^p(2)$ , namely  $450\text{ Mpa}$

One evaluates the criterion here following:  $\frac{SIPN1-SIPN2}{2}$

- with the formula of Basquin:  $grandeur\_equivalente=4098.3 \times (NBRUP^{-0.2693})$   
one finds  $NBRUP1=1255$  and for the damage:  $D1=7.968963E-04$  then  $NBRUP2=3652$  and for the damage:  $D2=2.738186E-04$  that is to say a total damage equal to:  $D=1.0707149E-03$
- with an interpolation of the curve of Wöhler:  
one finds  $NBRUP1=742$  and for the damage:  $D=1.347073E-03$  one finds  $NBRUP2=1742$  and for the damage:  $D=5.741842E-04$  that is to say a total damage equal to:  
 $D=1.9212575E-03$

'IFGEQ\_1': equivalent constraint of the first top of the under-cycle  $\sigma_{eq}(1)$  and

'SIGEQ\_2': equivalent constraint of the second top of the under-cycle  $\sigma_{eq}(2)$  :

One calculates the equivalent constraint for SIGEQ\_1:

$$\frac{\Delta \sigma_{eq}}{2} = \frac{1}{2} \max_{t_1} \max_{t_2} \sqrt{\frac{3}{2} (s(t_1) - s(t_2)) : (s(t_1) - s(t_2))} = 871.78\text{ MPa}$$

then for SIGEQ\_2 :

$$\frac{\Delta \sigma_{eq}}{2} = \frac{1}{2} \max_{t_1} \max_{t_2} \sqrt{\frac{3}{2} (s(t_1) - s(t_2)) : (s(t_1) - s(t_2))} = 653.83\text{ MPa}$$

And one evaluates the criterion here following:  $\frac{SIGEQ1-SIGEQ2}{2}$

- with the formula of Basquin:  $grandeur\_equivalente=4098.3 \times (NBRUP^{-0.2693})$   
one finds  $NBRUP1=313$  and for the damage:  $D1=3.1908789E-03$  then  $NBRUP2=912$  and for the damage:  $D2=1.0964061E-03$  that is to say a total damage equal to:  
 $D=4.287285E-03$
- with an interpolation of the curve of Wöhler:  
one finds  $NBRUP1=244$  and for the damage:  $D=4.1E-03$  one finds  $NBRUP2=582$  and for the damage:  $D=1.7175686E-03$  that is to say a total damage equal to:  $D=5.8176E-03$

## 2.7 Results of reference for modeling F

The results are got with the node  $NI$ .

- Results obtained with SOL\_NL :**

$t$	$\sigma_{xx}$	$\sigma_{yy}$	$\epsilon_{xx}^{tot}$	$\epsilon_{yy}^{tot}$	$\epsilon_{zz}^{tot}$
-----	---------------	---------------	-----------------------	-----------------------	-----------------------



0.00E+0	0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00
2.50E-1	3.00E+02	-1.50E+02	1.725E-03	-1.20E-03	-2.25E-04
5.00E-1	6.00E+02	-3.00E+02	3.45E-03	-2.40E-03	-4.50E-04
7.50E-1	9.00E+02	-4.50E+02	5.175E-03	-3.60E-03	-6.75E-04
1.00E+0	1.20E+03	-6.00E+02	6.90E-03	-4.80E-03	-9.00E-04
1.25E+0	9.00E+02	-4.50E+02	5.175E-03	-3.60E-03	-6.75E-04
1.50E+0	6.00E+02	-3.00E+02	3.45E-03	-2.40E-03	-4.50E-04
1.75E+0	3.00E+02	-1.50E+02	1.725E-03	-1.20E-03	-2.25E-04
2.00E+0	8.82E-26	8.82E-26	-7.92E-33	- 1. 39 E 32	-1.85E-32
2.25E+0	3.00E+02	-1.50E+02	1.725E-03	-1.20E-03	-2.25E-04
2.50E+0	6.00E+02	-3.00E+02	3.45E-03	-2.40E-03	-4.50E-04
2.75E+0	9.00E+02	- 4.5 0E+ 02	5 .1 75 E-0 3	- 3. 60 E-0 3	-6.75E-04
3.00E+0	6.00E+02	-3.00E+02	3.45E-03	-2.40E-03	-4.50E-04
3.25E+0	3.00E+02	-1.50E+02	1.725E-03	-1.20E-03	-2.25E-04
3.50E+0	7.88E-14	-5.15E-13	1.26E-18	-2.60E-18	3.52E-19

'EPSN1\_1' : normal deformation on the level associated with  $\sigma_1(1)$  first top of the under-cycle and

'EPSN1\_2' : normal deformation on the level associated with  $\sigma_1(2)$  second top of the under-cycle:

One uses the total half-deformation most important met at the time of the first under cycle, that is to say here 0.00345 and the total half-deformation most important met at the time of the second under cycle: 0.0025875 .

And one evaluates the criterion here following: 
$$\frac{|EPSN1 - EPSN2|}{2}$$

- with the formula of Manson:  $grandeur\_equivalente = 0,022524751 \times (NBRUP^{-0,1619})$   
one finds  $NBRUP1 = 107892$  and for the damage:  $D1 = 9.268535 E - 06$  one finds  $NBRUP2 = 637811$  and for the damage:  $D2 = 1.5678624479 E - 06$  that is to say a total damage equal to:  $D = 1.08363973 E - 05$
- with an interpolation of the curve of Manson-Whetstone sheath:  
one finds  $NBRUP1 = 36364$  and for the damage:  $D1 = 2.74994 E - 05$  one finds  $NBRUP2 = 193932$  and for the damage:  $D2 = 5.156443564 E - 06$  is a total damage equal to:  $D = 3.2655868578 E - 05$

'ETPR1\_1' : first principal total deflection of the first top of the under-cycle  $\epsilon_1^{tot}(1)$  and

'ETPR1\_2' : first principal total deflection of the second top of the under-cycle  $\epsilon_1^{tot}(2)$  :

One uses the total half-deformation most important met at the time of the first under cycle, that is to say here 0.00345 and the total half-deformation most important met at the time of the second under cycle: 0.0025875 .

And one evaluates the criterion here following: 
$$\frac{|ETPR1 - ETPR2|}{2}$$

- with the formula of Manson:  $grandeur\_equivalente = 0.022524751 \times (NBRUP^{-0,1619})$   
one finds  $NBRUP1 = 107892$  and for the damage:  $D1 = 9.268535 E - 06$  one finds  $NBRUP2 = 637811$  and for the damage:  $D2 = 1.5678624479 E - 06$  that is to say a total damage equal to:  $D = 1.08363973 E - 05$
- with an interpolation of the curve of Manson-Whetstone sheath:

one finds  $NBRUP1=36364$  and for the damage:  $DI=2.74994 E-05$  one finds  $NBRUP2=193932$  and for the damage:  $D2=5.156443564 E-06$  that is to say a total damage equal to:  $D=3.2655868578 E-05$

'ETEQ\_1': equivalent total deflection of the first top of the under-cycle  $\epsilon_{eq}^{tot}(1)$  and

'ETEQ\_2': equivalent total deflection of the second top of the under-cycle  $\epsilon_{eq}^{tot}(2)$

One calculates the equivalent total deflection for the first under-cycle with the formula:  $\epsilon_{eq} = \sqrt{\frac{2}{3}} e : e$  and

one finds  $\frac{1}{2} \epsilon_{eq}^{tot}(1) = 0.0034394767$ . For the second under-cycle:  $\frac{1}{2} \epsilon_{eq}^{tot}(2) = 0.0025796$

- with the formula of Manson:  $grandeur\_equivalente = 0.022524751 \times (NBRUP)^{-0.1619}$   
one finds  $NBRUP1=109947$  and for the damage:  $DI=9.09528647 E-06$  one finds  $NBRUP2=649960$  and for the damage:  $D2=1.5385558 E-06$  that is to say a total damage equal to:  $D=1.0633842276096 E-05$
- with an interpolation of the curve of Manson-Whetstone sheath:  
one finds  $NBRUP1=36929$  and for the damage:  $DI=2.707933 E-05$  one finds  $NBRUP2=197585$  and for the damage:  $D2=5.061111575 E-06$  that is to say a total damage equal to:  $D=3.214044324622 E-05$

• **Results obtained with SOL\_NL2 :**

$t$	$\sigma_{xx}$	$\epsilon_{xx}^{tot}$	$\epsilon_{yy}^{tot}$	$\epsilon_{zz}^{tot}$
0.00E+0	0.00E+00	0.00E+00	0.00E+00	0.00E+00
5.00E-1	6.00E+02	3.00E-03	-9.00E-04	-9.00E-04
1.00E+0	1.20E+03	1.05E-02	-4.05E-03	-4.05E-03
1.50E+0	6.00E+02	7.50E-03	-3.15E-03	-3.15E-03
2.00E+0	-9.12E+01	4.50E-03	-2.25E-03	-2.25E-03
2.5625E+0	-6.75E+02	-1.91E-13	-6.75E-04	-6.75E-04
3.0625E+0	1.125E+02	3.9375E-03	-1.86E-03	-1.86E-03
3.5625E+0	9.00E+02	7.875E-03	-3.0375E-03	-3.0375E-03
4.0625E+0	1.125E+02	3.9375E-03	-1.86 E-03	-1.86 E-03
4.5625E+0	-6.75E+02	-1.91E-13	-6.75 E-04	-6.75E-04

'EPSN1\_1': normal deformation on the level associated with  $\sigma_1(1)$  first top of the under-cycle and

'EPSN1\_2': normal deformation on the level associated with  $\sigma_1(2)$  second top of the under-cycle:

The dem is used the total I-deformation most important met at the time of the first under cycle, is here 0.00525 and the half total deflection most important met at the time of the second under cycle: 0.0039375.

And one evaluates the criterion here following:  $\frac{|EPSN1 - EPSN2|}{2}$

- with the formula of Manson:  $grandeur\_equivalente = 0.022524751 \times (NBRUP)^{-0.1619}$   
one finds  $NBRUP1=8067$  and for the damage:  $DI=1.239547 E-04$  one finds  $NBRUP2=47691$  and for the damage:  $D2=2.0968145 E-05$  that is to say a total damage equal to:  $D=1.449229 E-04$

- with an interpolation of the curve of Manson-Whetstone sheath:  
one finds  $NBRUP1=5260$  and for the damage:  $DI=1.901065 E-04$  one finds  
 $NBRUP2=19698$  and for the damage:  $D2=5.0767 E-05$  that is to say a total damage equal to:  
 $D=2.408735 E-04$

'ETPR1\_1' : first principal total deflection of the first top of the under-cycle  $\epsilon_1^{tot}(1)$  and

'ETPR1\_2' : first principal total deflection of the second top of the under-cycle  $\epsilon_1^{tot}(2)$  :

One uses the total half-deformation most important met at the time of the first under cycle, that is to say here  
0.00345 and the total half-deformation most important met at the time of the second under cycle:  
0.0025875 .

And one evaluates the criterion here following:  $\frac{|ETPR1-ETPR2|}{2}$

- with the formula of Manson:  $grandeur\_equivalente=0.022524751 \times (NBRUP^{-0.1619})$   
one finds  $NBRUP1=8067$  and for the damage:  $DI=1.239547 E-04$  one finds  
 $NBRUP2=47691$  and for the damage:  $D2=2.0968145 E-05$  that is to say a total damage equal  
to:  $D=1.449229 E-04$
- with an interpolation of the curve of Manson-Whetstone sheath:  
one finds  $NBRUP1=5260$  and for the damage:  $DI=1.901065 E-04$  one finds  
 $NBRUP2=19698$  and for the damage:  $D2=5.0767 E-05$  that is to say a total damage equal to:  
 $D=2.408735 E-04$

'ETEQ\_1' : equivalent total deflection of the first top of the under-cycle  $\epsilon_{eq}^{tot}(1)$  and

'ETEQ\_2' : equivalent total deflection of the second top of the under-cycle  $\epsilon_{eq}^{tot}(1)$

One calculates the equivalent total deflection for the first under-cycle with the formula:  $\epsilon_{eq} = \sqrt{\frac{2}{3} e : e}$  and

one finds  $\frac{1}{2} \epsilon_{eq}^{tot}(1) = 0.004625$  . For the second under-cycle, one finds  $\frac{1}{2} \epsilon_{eq}^{tot}(2) = 0.0034125$


- with the formula of Manson:  $grandeur\_equivalente=0.022524751 \times (NBRUP^{-0.1619})$   
one finds  $NBRUP1=17650$  and for the damage:  $DI=5.6657 E-05$  one finds  
 $NBRUP2=115427$  and for the damage:  $D2=8.66351 E-06$  that is to say a total damage equal to:  
 $D=6.53204991 E-05$
- with an interpolation of the curve of Manson-Whetstone sheath:  
one finds  $NBRUP1=9411$  and for the damage:  $DI=1.062557 E-04$  one finds  
 $NBRUP2=38423$  and for the damage:  $D2=2.60258665 E-05$  that is to say a total damage equal  
to:  $D=1.322816 E-04$

• **Results obtained with SOL\_NL3 :**

t	$\sigma_{xx}$	$\epsilon_{xx}^{tot}$	$\epsilon_{yy}^{tot}$	$\epsilon_{zz}^{tot}$	$\epsilon_{xx}^p$	$\epsilon_{yy}^p$	$\epsilon_{zz}^p$
0.00E+0	0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00	0.00E+00
5.00E-1	9.00E+02	4.50E-03	-1.35E-03	-1.35E-03	1.51E-18	1.09E-18	-7.51E-19
1.00E+0	1.80E+03	2.25E-02	-9.45E-03	-9.45E-03	1.35E-02	-6.75E-03	-6.75E-03

1.50E+0	6.00E+02	1.65E-02	-7.65E-03	-7.65E-03	1.35E-02	-6.75E-03	-6.75E-03
2.00E+0	-6.00E+02	1.50E-03	-1.35E-03	-1.35E-03	4.50E-03	-2.25E-0	-2.25E-0
2.50E+0	9.00E+02	9.00E-03	-3.60E-03	-3.60E-03	4.50E-03	3	3
3.00E+0	2.40E+03	3.45E-02	-1.485E-02	-1.485E-02	2.25E-02	-2.25E-03	-2.25E-03
3.50E+0	6.00E+02	2.55E-02	-1.215E-02	-1.215E-02	2.25E-02	-1.125E-02	-1.125E-02
3.91667E+0	-9.00E+02	-4.50E-03	1.35E-03	1.35E-03	-5.55E-11	-1.125E-02	-1.125E-02
						2.69E-11	2.86E-11

With this intention a better idea of what interests us here, namely  $\epsilon_{xx}^p$  since the maximum values of the plastic deformation are according to the direction  $xx$ , here evolution of  $\epsilon_{xx}^p$  according to time:

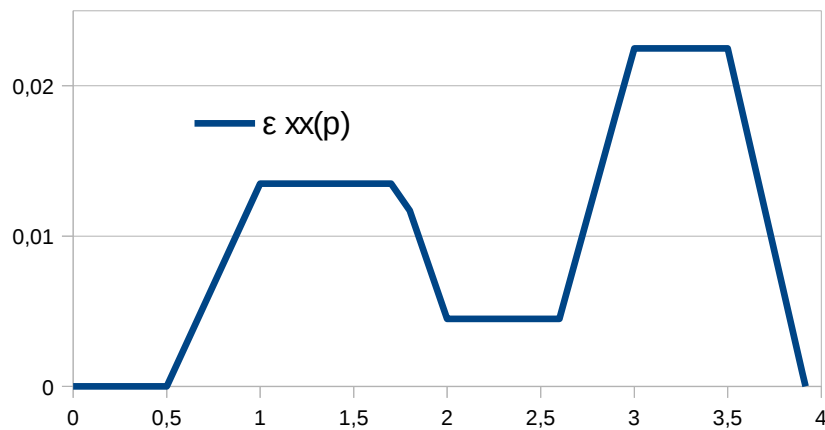

'EPPR1\_1': first principal plastic deformation of the first top of the under-cycle  $\epsilon_1^p(1)$  and

'EPPR1\_2': first principal plastic deformation of the second top of the under-cycle  $\epsilon_1^p(2)$  :

One evaluates the criterion here following:  $\frac{|EPPR1 - EPPR2|}{2}$


Attention, here the value of  $\epsilon_{xx}^p$  is not worthless at the end of the first under cycle, therefore for  $\frac{EPPR1}{2}$

one obtains:  $\frac{0.0135 - 0.0045}{2} = 0.0045$ . For  $\frac{EPPR2}{2}$ , one obtains more directly: 0,01125.

- with the formula of Manson:  $grandeur\_equivalente = 0.022524751 \times (NBRUP^{-0.1619})$   
one finds  $NBRUP1 = 20905$  and for the damage:  $D1 = 4.7836 E - 05$  one finds  $NBRUP2 = 73$   
and for the damage:  $D2 = 1.37307 E - 02$  that is to say a total damage equal to:  
 $D = 1.377855 E - 02$
- with an interpolation of the curve of Manson-Whetstone sheath:  
one finds  $NBRUP1 = 10672$  and for the damage:  $D1 = 9.37 E - 05$  one finds  $NBRUP2 = 478$  and  
for the damage:  $D2 = 2.0921444 E - 03$  that is to say a total damage equal to:  
 $D = 2.185844 E - 03$

## 2.8 Results of reference for modeling G

The analytical solutions of the orientation of the plan criticizes are in [bib4]. Orientation of the plan critical is defined by angles ( $\phi_x, \phi_y, \phi_z$ ) between the normal vector of the critical plan and axes as shown in the figure above.

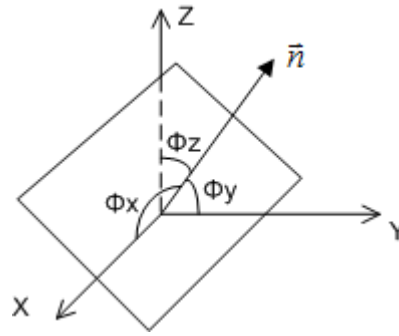

One notes that for the criteria `DANG_VAN_MODI_AC` and of `MATAKE_MODI_AC`, the critical plan is it plan maximum shearing. For the criteria of `DANG_VAN_MODI_AV`, of `MATAKE_MODI_AC` and of `FATESOCI_MODI_AV` the critical plan is the plan of the maximum damage.

With the conditions of the loading listed in Section 1.4.6, the analytical solutions of reference for this modeling are the following ones

- Criterion of `DANG_VAN_MODI_AC`  
The angle enters the vector normal of the critical plan and the axis  $Z$  is 45 degrees.
- Criterion of `MATAKE_MODI_AC`  
The angle enters the vector normal of the critical plan and the axis  $Z$  is 45 degrees.
- Criterion of `DANG_VAN_MODI_AV`  
The angle enters the vector normal of the critical plan and the axis  $Z$  is 45 degrees.
- Criterion of `MATAKE_MODI_AV`  
The angle enters the vector normal of the critical plan and the axis  $Z$  according to  $\alpha$  is

$$\phi_z = \arccos\left(\frac{\sqrt{2}}{2} \sqrt{1 - \sqrt{1 - \frac{1}{a^2 + 2a^2\alpha + a^2\alpha^2 + 1}}}\right)$$

where  $a$  is a property matériel obtained by the parameter `MATAKE_A` and  $a=0.05$  is used in this case test.

- Criterion of `FATESOCI_MODI_AV`  
The angle enters the vector normal of the critical plan and the axis  $Z$  according to  $\alpha$  is

$$\phi_z = \arccos\left(\frac{\sqrt{2}}{4} \sqrt{5 + A_1 - \sqrt{1 + A_1^2 + 8}}\right)$$

with  $A_1 = \frac{2S_y}{a\sigma_{x,a}(1+\alpha)}$ . Elastic limit  $S_y = 208 \text{ MPa}$  and  $a = 0.05$ . Therefore, the parameter of `FATSOC_A` is  $a/S_y = 0.00024$

## 2.9 Results of reference for modeling H

In this modeling, the results of reference analytical and are given in the table below.

Let us define certain sizes first of all:

- the diverter of the tensor of the constraints:  $s = \sigma - \frac{1}{3} \text{tr}(\sigma) \cdot \mathbf{I}$  where  $\mathbf{I}$  is the matrix identity
- the diverter of the tensor of the deformations:  $e = \epsilon - \frac{1}{3} \text{tr}(\epsilon) \cdot \mathbf{I}$  where  $\mathbf{I}$  is the matrix identity

*It is stressed that the results in interval of time between 0 and 1 second are for the monotonous part of loading and are not taken into account in the calculation of the sizes for the cyclic behavior.*

**It is noted that there exist two types of shearing strains: the type of engineering  $\gamma_{ij}$  ( $i \neq j$ ) and its tensorial type  $\epsilon_{ij}$  ( $i \neq j$ ). To note that  $\gamma_{ij} = 2\epsilon_{ij}$ . For 'DGAMCR', 'MGAMCR', 'MGAMPC', one used the deformations of the type of engineering  $\gamma_{ij}$ .**

Sizes	'SIGEQ1'	'ENDO1'	'NBRUP1'	'VNM1X', 'VNM1Y', 'VNM1Z'
'DTAUCR'	100 MPa	1.028E-6	9.73E5	(0,707, -0,707), 0,707.0
'DGAMCR'	9.73E5	1.583E-4	6.3163E3	(0,707, -0,707), 0,707.0
'DSINCR'	200	1.348E-5	7.418E4	(- 1.1), 0.0174,0
'DEPNCR'	1.75E-3	2.11E-5	4.74E4	(- 1, 1), 0.0174,0
'MTAUCR'	100 MPa	1.028E-6	9.73E5	(0,707, -0,707), 0,707.0
'MGAMCR'	9.73E5	1.583E-4	6.3163E3	(0,707, -0,707), 0,707.0
'MSINCR'	200	1.348E-5	7.418E4	(- 1.1), 0.0174,0
'MEPNCR'	1.75E-3	2.11E-5	4.74E4	(- 1, 1), 0.0174,0
'DGAMPC'	1.125E-3	1.3782E-6	7.256E5	(0,707, -0,707), 0,707.0
'DEPNPC'	0.75E-3	1.126E-7	8.88E6	(- 1.1), 0.0174,0
'MGAMPC'	1.125E-3	1.3782E-6	7.256E5	(0,707, -0,707), 0,707.0
'MEPNPC'	0.75E-3	1.126E-7	8.88E6	(- 1.1), 0.0174,0

## 2.10 Bibliographical references

1. ANGLES J. "multiaxial Criteria of starting in fatigue to great number D cycles, critical plan, DANG VAN", Project FATMAV, Notes EDF HT-64/03/015A, 2003
2. ANGLES J., PAPACONSTANTINO T. "multiaxial Criteria of starting in fatigue to great number D cycles under nonperiodic loading", Project FATMAV, Note EDF HT-64/04/006A, 2004
3. ANGLES J. "Synthesis on the criteria of starting in fatigue multiaxial to great number D cycles developed in *Code\_Aster*", Project Tires Thermal, Notes EDF HT-64/05/019A, 2005
4. LEI B., TRAN V. - X. "Carryforward one the 2<sup>Nd</sup> semi-annual meeting for the collaborative PhD project between EDF R & D and Tsinghua University (July 2012 – January 2013)", Report CR-AMA-13.021


## 3 Modeling A

---

### 3.1 Characteristics of modeling

This CAS-test tests criteria `MATAKE_MODI_AC`, `DANG_VAN_MODI_AC`, `VMIS_TRESCA`, criterion formulates some for periodic and biaxial loading proportional;

### 3.2 Characteristics of the grid

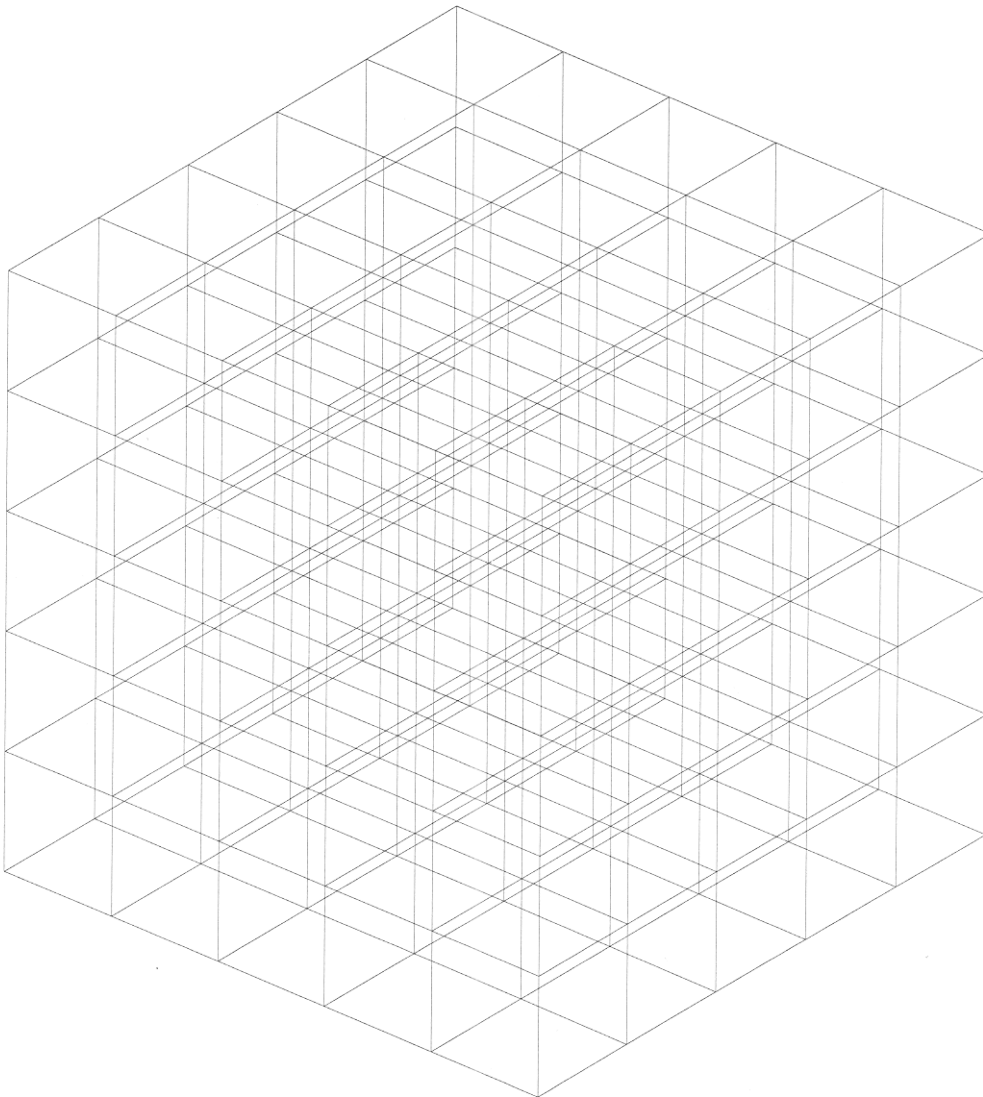

Modeling 3D : 125 quadratic elements of volume: HEXA8.

**Figure of the grid of the cube**

The grid of the cube was obtained starting from the version 2000 of maillor GIBI.

Many nodes: 216  
Many meshes: 465



## 3.3 Sizes tested and results

- Criterion 'MATAKE\_MODI\_AC' and associated criterion in formula:

For the results with the node  $NI$  and with the mesh  $M60$  (not Gauss 3)

The option `COURBE_GRD_VIE` = 'WOHLER' and

The option `COURBE_GRD_VIE` = 'FORMES\_VIE' and `FORMULE_VIE` = WHOL:

Identification	Type of reference	Value of reference	Tolerance
$\Delta \tau(n_1)$	'ANALYTICAL'	1.500000E+02	1.0E-10
component $x$ of $n_1$	'ANALYTICAL'	-7.071068E-01	1.0E-10
component $y$ of $n_1$	'ANALYTICAL'	7.071068E-01	1.0E-10
component $z$ of $n_1$	'ANALYTICAL'	0.0	1.0E-10
$N_{\max}(n_1)$	'ANALYTICAL'	5.000000E+01	1.0E-10
$N_m(n_1)$	'ANALYTICAL'	0.0	1.0E-10
$\varepsilon_{\max}(n_1)$	'ANALYTICAL'	1.750000E-04	1.0E-10
$\varepsilon_m(n_1)$	'ANALYTICAL'	0.0	1.0E-10
$\sigma_{eq}(n_1)$	'ANALYTICAL'	3.000000E+02	1.0E-10
$Nb_{cr}(n_1)$	'ANALYTICAL'	1.094600E+04	1.0E-10
$ENDO(n_1)$	'ANALYTICAL'	9.135647E-05	1.0E-10
$\Delta \tau(n_2)$	'ANALYTICAL'	1.500000E+02	1.0E-10
component $x$ of $n_2$	'ANALYTICAL'	7.071068E-01	1.0E-10
component $y$ of $n_2$	'ANALYTICAL'	7.071068E-01	1.0E-10
component $z$ of $n_2$	'ANALYTICAL'	0.0	1.0E-10
$N_{\max}(n_2)$	'ANALYTICAL'	5.000000E+01	1.0E-10
$N_m(n_2)$	'ANALYTICAL'	0.0	1.0E-10
$\varepsilon_{\max}(n_2)$	'ANALYTICAL'	1.750000E-04	1.0E-10
$\varepsilon_m(n_2)$	'ANALYTICAL'	0.0	1.0E-10
$\sigma_{eq}(n_2)$	'ANALYTICAL'	3.000000E+02	1.0E-10
$Nb_{cr}(n_2)$	'ANALYTICAL'	1.094600E+04	1.0E-10
$ENDO(n_2)$	'ANALYTICAL'	9.135647E-05	1.0E-10

The option `COURBE_GRD_VIE` = 'FORMES\_VIE' and `FORMULE_VIE` = WHOL\_F:

Identification	Type of reference	Value of reference	Tolerance
$\Delta \tau(n_1)$	'ANALYTICAL'	1 . 500000E + 02	1.0E-10
component $x$ of $n_1$	'ANALYTICAL'	- 7.071068E - 01	1.0E-10
component $y$ of $n_1$	'ANALYTICAL'	7.071068E - 01	1.0E-10
component $z$ of $n_1$	'ANALYTICAL'	0.0	1.0E-10
$N_{\max}(n_1)$	'ANALYTICAL'	5.000000E+01	1.0E-10
$N_m(n_1)$	'ANALYTICAL'	0.0	1.0E-10
$\varepsilon_{\max}(n_1)$	'ANALYTICAL'	1.750000E - 04	1.0E-10
$\varepsilon_m(n_1)$	'ANALYTICAL'	0.0	1.0E-10
$\sigma_{eq}(n_1)$	'ANALYTICAL'	3.000000E+02	1.0E-10
$Nb_{cr}(n_1)$	'ANALYTICAL'	1.094600E+04	4.0E-03
$ENDO(n_1)$	'ANALYTICAL'	1.6519E+04	4.0E-03
$\Delta \tau(n_2)$	'ANALYTICAL'	6.05356E-05	1.0E-10
component $x$ of $n_2$	'ANALYTICAL'	7.071068E - 01	1.0E-10
component $y$ of $n_2$	'ANALYTICAL'	7.071068E - 01	1.0E-10
component $z$ of $n_2$	'ANALYTICAL'	0.0	1.0E-10
$N_{\max}(n_2)$	'ANALYTICAL'	5.000000E+01	1.0E-10
$N_m(n_2)$	'ANALYTICAL'	0.0	1.0E-10
$\varepsilon_{\max}(n_2)$	'ANALYTICAL'	1.750000E - 04	1.0E-10
$\varepsilon_m(n_2)$	'ANALYTICAL'	0.0	1.0E-10
$\sigma_{eq}(n_2)$	'ANALYTICAL'	3.000000E+02	1.0E-10
$Nb_{cr}(n_2)$	'ANALYTICAL'	1.6519E+04	4.0E-03
$ENDO(n_2)$	'ANALYTICAL'	6.05356E-05	4.0E-03

• **Criterion 'DANG\_VAN\_MODI\_AC' and associated criterion in formula:**

For the results **with the node NI** and with mesh **M60 (not Gauss 3)**

The option COURBE\_GRD\_VIE = 'WOHLER' and

The option COURBE\_GRD\_VIE = 'FORMES\_VIE' and FORMULE\_VIE = 'WHOL' :

Identification	Type of reference	Value of reference	Tolerance
$\Delta \tau(n_1)$	'ANALYTICAL'	1 . 500000E + 02	1.0E-10

component $x$ of $n_1$	'ANALYTICAL'	7.071068E – 01	1.0E-10
component $y$ of $n_1$	'ANALYTICAL'	7.071068E – 01	1.0E-10
component $z$ of $n_1$	'ANALYTICAL'	0.0	1.0E-10
$N_{\max}(n_1)$	'ANALYTICAL'	5.000000E+01	1.0E-10
$N_m(n_1)$	'ANALYTICAL'	0.0	1.0E-10
$\varepsilon_{\max}(n_1)$	'ANALYTICAL'	1.750000E – 04	1.0E-10
$\varepsilon_m(n_1)$	'ANALYTICAL'	0.0	1.0E-10
$\sigma_{eq}(n_1)$	'ANALYTICAL'	2.750000E+02	1.0E-10
$Nb_{cr}(n_1)$	'ANALYTICAL'	1.490300E+04	1.0E-10
$ENDO(n_1)$	'ANALYTICAL'	6.709959E – 05	1.0E-10
$\Delta \tau(n_2)$	'ANALYTICAL'	1 . 500000E + 02	1.0E-10
component $x$ of $n_2$	'ANALYTICAL'	– 7.071068E – 01	1.0E-10
component $y$ of $n_2$	'ANALYTICAL'	7.071068E – 01	1.0E-10
component $z$ of $n_2$	'ANALYTICAL'	0.0	1.0E-10
$N_{\max}(n_2)$	'ANALYTICAL'	5.000000E+01	1.0E-10
$N_m(n_2)$	'ANALYTICAL'	0.0	1.0E-10
$\varepsilon_{\max}(n_2)$	'ANALYTICAL'	1.750000E – 04	1.0E-10
$\varepsilon_m(n_2)$	'ANALYTICAL'	0.0	1.0E-10
$\sigma_{eq}(n_2)$	'ANALYTICAL'	2.750000E+02	1.0E-10
$Nb_{cr}(n_2)$	'ANALYTICAL'	1.490300E+04	1.0E-10
$ENDO(n_2)$	'ANALYTICAL'	6.709959E – 05	1.0E-10

The option COURBE\_GRD\_VIE = 'FORMES\_VIE' and FORMULE\_VIE = WHOL\_F:

Identification	Type of reference	Value of reference	Tolerance
$\Delta \tau(n_1)$	'ANALYTICAL'	1 . 500000E + 02	1.0E-10
component $x$ of $n_1$	'ANALYTICAL'	7.071068E – 01	1.0E-10
component $y$ of $n_1$	'ANALYTICAL'	7.071068E – 01	1.0E-10
component $z$ of $n_1$	'ANALYTICAL'	0.0	1.0E-10
$N_{\max}(n_1)$	'ANALYTICAL'	5.000000E+01	1.0E-10

$N_m(n_1)$	'ANALYTICAL'	0.0	1.0E-10
$\varepsilon_{\max}(n_1)$	'ANALYTICAL'	1.750000E - 04	1.0E-10
$\varepsilon_m(n_1)$	'ANALYTICAL'	0.0	1.0E-10
$\sigma_{eq}(n_1)$	'ANALYTICAL'	2.750000E+02	1.0E-10
$Nb_{cr}(n_1)$	'ANALYTICAL'	2.2822E+04	5.0E-03
$ENDO(n_1)$	'ANALYTICAL'	4.381737E-05	5.0E-03
$\Delta \tau(n_2)$	'ANALYTICAL'	1 . 500000E + 02	1.0E-10
component $x$ of $n_2$	'ANALYTICAL'	- 7.071068E - 01	1.0E-10
component $y$ of $n_2$	'ANALYTICAL'	7.071068E - 01	1.0E-10
component $z$ of $n_2$	'ANALYTICAL'	0.0	1.0E-10
$N_{\max}(n_2)$	'ANALYTICAL'	5.000000E+01	1.0E-10
$N_m(n_2)$	'ANALYTICAL'	0.0	1.0E-10
$\varepsilon_{\max}(n_2)$	'ANALYTICAL'	1.750000E - 04	1.0E-10
$\varepsilon_m(n_2)$	'ANALYTICAL'	0.0	1.0E-10
$\sigma_{eq}(n_2)$	'ANALYTICAL'	2.750000E+02	1.0E-10
$Nb_{cr}(n_2)$	'ANALYTICAL'	2.2822E+04	5.0E-03
$ENDO(n_2)$	'ANALYTICAL'	4.381737E-05	5.0E-03

• **Criterion ' VMIS\_TRESCA '**

For nodes: N1; N206; Mesh: M60 ( Not Gauss: 3)

Identification	Type of reference	Value of reference	Tolerance
$\sigma_{xx}$ (Moment: 3)	'ANALYTICAL'	- 1.00000E+02	1.0E-10
$\sigma_{yy}$ (Moment: 3)	'ANALYTICAL'	2.00000E+02	1.0E-10
$\sigma_s$ (VMIS)	'ANALYTICAL'	529.15026E+02	1.0E-10
$\sigma_s$ (TRESCA)	'ANALYTICAL'	600.00000E+02	1.0E-10

For nodes: N1; N206; Mesh: M60 (Not of Gauss: 7)

Identification	Type of reference	Value of reference	Tolerance
$\sigma_{xx}$ (Moment: 3)	'ANALYTICAL'	- 1.00000E+02	1.0E-10
$\sigma_{yy}$ (Moment: 3)	'ANALYTICAL'	2.00000E+02	1.0E-10

$\sigma_s$ (VMIS)	'ANALYTICAL'	529.15026E+02	1.0E-10
$\sigma_s$ (TRESCA)	'ANALYTICAL'	600.00000E+02	1.0E-10

- **Criterion formulates some finding** `VMIS\_TRESCA`

Results with the node *NI* and with mesh *M60* (not Gauss 3 and 7)

Identification	Type of reference	Value of reference	Tolerance
$\sigma_s$ (VMIS)	'ANALYTICAL'	529.15026E+02	1.0E-10

## 4 Modeling B

### 4.1 Characteristics of modeling

This test of the criteria CAS-tests MATAKE\_MODI\_AV, DANG\_VAN\_MODI\_AV, FATESOCI\_MODI\_AV, criterion formulates some for the loading not-periodical and biaxial and propotional;

### 4.2 Characteristics of the grid

Identical to modeling A.

### 4.3 Sizes tested and results

- Criterion 'MATAKE\_MODI\_AV' and associated criterion in formula

For the results with the node *N206* and with mesh *M60* (not Gauss 3)

The option COURBE\_GRD\_VIE='WOHLER' and L

The option COURBE\_GRD\_VIE = 'FORMES\_VIE' and FORMULE\_VIE = WHOL:

Identification	Type of reference	Value of reference
component $x$ of $n_1$ and $n_2$	'AUTRE_ASTER'	-0.38268343236509 0.38268343236509
component $y$ of $n_1$ and $n_2$	'AUTRE_ASTER'	0.92718385456679 0.92387953251129
component $z$ of $n_1$ and $n_2$	'AUTRE_ASTER'	0.00000000000000E+00
$ENDO(n_1)$	'AUTRE_ASTER'	7.0532362250863E-04

In the table above, the components  $x$  and  $y$  of  $n_1$  and  $n_2$  two values have because there exist two vectors which correspond to the same value of damage  $ENDO(n_1) = ENDO(n_2)$ .

The option COURBE\_GRD\_VIE= 'FORMES\_VIE' and FORMULE\_VIE = WHOL\_F:

Identification	Type of reference	Value of reference
component $x$ of $n_1$ and $n_2$	'AUTRE_ASTER'	-0.38268343236509 0.38268343236509
component $y$ of $n_1$ and $n_2$	'AUTRE_ASTER'	0.92718385456679 0.92387953251129
component $z$ of $n_1$ and $n_2$	'AUTRE_ASTER'	0.00000000000000E+00
$ENDO(n_1)$	'AUTRE_ASTER'	3.3180845213285E-04

In the table above, the components  $x$  and  $y$  of  $n_1$  and  $n_2$  two values have because there exist two vectors which correspond to the same value of damage  $ENDO(n_1) = ENDO(n_2)$ .

- Criterion 'DANG\_VAN\_MODI\_AV' and associated criterion in formula

For the results with the node *N206* and with mesh *M60* (not Gauss 3)

Option COURBE\_GRD\_VIE='WOHLER' and

The option COURBE\_GRD\_VIE='FORMES\_VIE' and FORMULE\_VIE = WHOL:

Identification	Type of reference	Value of reference
component $x$ of $n_1$ and $n_2$	'AUTRE_ASTER'	-7.0710678118655E-01 7.0710678118655E-01
component $y$ of $n_1$ and $n_2$	'AUTRE_ASTER'	7.0710678118655E-01
component $z$ of $n_1$ and $n_2$	'AUTRE_ASTER'	0.0000000000000E+00
$ENDO(n_1)$	'AUTRE_ASTER'	1.3419917535855E-04

In the table above, the components  $x$  and  $y$  of  $n_1$  and  $n_2$  two values have because there exist two vectors which correspond to the same value of damage  $ENDO(n_1) = ENDO(n_2)$ .

The option COURBE\_GRD\_VIE = 'FORMES\_VIE' and FORMULE\_VIE = WHOL\_F:

Identification	Type of reference	Value of reference
component $x$ of $n_1$ and $n_2$	'AUTRE_ASTER'	-7.0710678118655E-01 7.0710678118655E-01
component $y$ of $n_1$ and $n_2$	'AUTRE_ASTER'	7.0710678118655E-01
component $z$ of $n_1$ and $n_2$	'AUTRE_ASTER'	0.0000000000000E+00
$ENDO(n_1)$	'AUTRE_ASTER'	8.7960237413997E-05

In the table above, the components  $x$  and  $y$  of  $n_1$  and  $n_2$  two values have because there exist two vectors which correspond to the same value of damage  $ENDO(n_1) = ENDO(n_2)$ .

- **Criterion 'FATESOCI\_MODI\_AV' and associated criterion in formula:**

For the results with the node  $NI$  and with mesh  $M60$  (not Gauss 3)

The option COURBE\_GRD\_VIE = 'WOHLER' and

The option COURBE\_GRD\_VIE = 'FORMES\_VIE' and FORMULE\_VIE = MANCO1:

Identification	Type of reference	Value of reference
component $x$ of $n_1$ and $n_2$	'AUTRE_ASTER'	-0.43051109680829 0.43051109680830
component $y$ of $n_1$ and $n_2$	'AUTRE_ASTER'	0.90258528434986
component $z$ of $n_1$ and $n_2$	'AUTRE_ASTER'	0
$ENDO(n_1)$	'AUTRE_ASTER'	0.43649132038876

In the table above, the component  $x$  of  $n_1$  and  $n_2$  has two values because there exist two vectors which correspond to the same value of damage  $ENDO(n_1) = ENDO(n_2)$ .

## 5 Modeling C

### 5.1 Characteristics of modeling

The criterion in formula makes it possible to find the criteria 'MATAKE\_MODI\_AC' and 'DANG\_VAN\_MODI\_AV' and of the criterion in formula associated for the loading multiaxial.

### 5.2 Characteristics of the grid

The grid is identical to that of modeling A.

### 5.3 Sizes tested and results

For periodic loading:

For the results with mesh *M60* (not Gauss 3) for the option COURBE\_GRD\_VIE = 'WOHLER' and for the option COURBE\_GRD\_VIE = 'FORMES\_VIE' and FORMULE\_VIE = WHOL:

Identification	Type of reference	Value of reference
$\Delta \tau(n_1)$	'NON_REGRESSION'	1.330171E + 02
component <i>x</i> of $n_1$	'NON_REGRESSION'	6.972459E - 02
component <i>y</i> of $n_1$	'NON_REGRESSION'	9.969556E - 01
component <i>z</i> of $n_1$	'NON_REGRESSION'	- 3.489950E - 02
$N_{\max}(n_1)$	'NON_REGRESSION'	2.357226E+00
$N_m(n_1)$	'NON_REGRESSION'	2.220625E - 14
$\varepsilon_{\max}(n_1)$	'NON_REGRESSION'	0.000000 E + 00
$\varepsilon_m(n_1)$	'NON_REGRESSION'	- 3.627373E - 05
$\sigma_{eq}(n_1)$	'NON_REGRESSION'	2.348841E+02
$Nb_{cr}(n_1)$	'NON_REGRESSION'	2.583800E+04
$ENDO(n_1)$	'NON_REGRESSION'	3.870305E - 05
$\Delta \tau(n_2)$	'NON_REGRESSION'	1.330158E + 02
component <i>x</i> of $n_2$	'NON_REGRESSION'	- 9.901402E - 01
component <i>y</i> of $n_2$	'NON_REGRESSION'	6.906669E - 02
component <i>z</i> of $n_2$	'NON_REGRESSION'	1.218693E - 01
$N_{\max}(n_2)$	'NON_REGRESSION'	1.264927E+02
$N_m(n_2)$	'NON_REGRESSION'	1.581158E +0 1
$\varepsilon_{\max}(n_2)$	'NON_REGRESSION'	6.474850E - 04



$\varepsilon_m(n_2)$	'NON_REGRESSION'	8.093563E - 05
$\sigma_{eq}(n_2)$	'NON_REGRESSION'	3.892627E+02
$Nb_{cr}(n_2)$	'NON_REGRESSION'	3.323100E+04
$ENDO(n_2)$	'NON_REGRESSION'	3.009210E - 05

For the results with mesh *M60* (not Gauss 3) for the option COURBE\_GRD\_VIE = 'FORMES\_VIE' and FORMULE\_VIE = WHOL\_F:

Identification	Type of reference	Value of reference
$\Delta \tau(n_1)$	'NON_REGRESSION'	1.330171E + 02
component <i>x</i> of $n_1$	'NON_REGRESSION'	6.972459E - 02
component <i>y</i> of $n_1$	'NON_REGRESSION'	9.969556E - 01
component <i>z</i> of $n_1$	'NON_REGRESSION'	- 3.489950E - 02
$N_{max}(n_1)$	'NON_REGRESSION'	2.357226E+00
$N_m(n_1)$	'NON_REGRESSION'	2.220625E - 14
$\varepsilon_{max}(n_1)$	'NON_REGRESSION'	0.000000 E + 00
$\varepsilon_m(n_1)$	'NON_REGRESSION'	- 3.627373E - 05
$\sigma_{eq}(n_1)$	'NON_REGRESSION'	2.348841E+02
$Nb_{cr}(n_1)$	'NON_REGRESSION'	5.1477E+04
$ENDO(n_1)$	'NON_REGRESSION'	1.9426163934314E-05
$\Delta \tau(n_2)$	'NON_REGRESSION'	1.330158E + 02
component <i>x</i> of $n_2$	'NON_REGRESSION'	- 9.901402E - 01
component <i>y</i> of $n_2$	'NON_REGRESSION'	6.906669E - 02
component <i>z</i> of $n_2$	'NON_REGRESSION'	1.218693E - 01
$N_{max}(n_2)$	'NON_REGRESSION'	1.264927E+02
$N_m(n_2)$	'NON_REGRESSION'	1.581158E +0 1
$\varepsilon_{max}(n_2)$	'NON_REGRESSION'	6.474850E - 04
$\varepsilon_m(n_2)$	'NON_REGRESSION'	8.093563E - 05
$\sigma_{eq}(n_2)$	'NON_REGRESSION'	3.892627E+02
$Nb_{cr}(n_2)$	'NON_REGRESSION'	5.1477E+04
$ENDO(n_2)$	'NON_REGRESSION'	1.9426163934314E-05

For the results with the node *N214* for the option COURBE\_GRD\_VIE=' WOHLER' and for the option COURBE\_GRD\_VIE = 'FORMES\_VIE' and FORMULE\_VIE = WHOL:

Identification	Type of reference	Value of reference
$\Delta \tau(n_1)$	'NON_REGRESSION'	1.1557902030140E+02
component <i>x</i> of $n_1$	'NON_REGRESSION'	3.8280107156988E-01
component <i>y</i> of $n_1$	'NON_REGRESSION'	8.4447216637038E-01
component <i>z</i> of $n_1$	'NON_REGRESSION'	3.7460659341591E-01
$N_{\max}(n_1)$	'NON_REGRESSION'	7.3701737537055E+01
$N_m(n_1)$	'NON_REGRESSION'	-6.6290480086559E+00
$\varepsilon_{\max}(n_1)$	'NON_REGRESSION'	0.
$\varepsilon_m(n_1)$	'NON_REGRESSION'	-4.2254262706848E-05
$\sigma_{eq}(n_1)$	'NON_REGRESSION'	2.8392113675768E+02
$Nb_{cr}(n_1)$	'NON_REGRESSION'	1.3505000000000E+04
<i>ENDO</i> ( $n_1$ )	'NON_REGRESSION'	7.4047664409136E-05
$\Delta \tau(n_2)$	'NON_REGRESSION'	1.1520977056656E+02
component <i>x</i> of $n_2$	'NON_REGRESSION'	-9.1924333354254E-01
component <i>y</i> of $n_2$	'NON_REGRESSION'	3.9019564505737E-01
component <i>z</i> of $n_2$	'NON_REGRESSION'	5.2335956242944E-02
$N_{\max}(n_2)$	'NON_REGRESSION'	1.1296755026397E+02
$N_m(n_2)$	'NON_REGRESSION'	6.8110853707598E+00
$\varepsilon_{\max}(n_2)$	'NON_REGRESSION'	3.6085283407484E-04
$\varepsilon_m(n_2)$	'NON_REGRESSION'	4.5106604259354E-05
$\sigma_{eq}(n_2)$	'NON_REGRESSION'	3.4226598124581E+02
$Nb_{cr}(n_2)$	'NON_REGRESSION'	4.8720000000000E+03
<i>ENDO</i> ( $n_2$ )	'NON_REGRESSION'	2.0525129321838E-04

For the results with the node *N214* for the option COURBE\_GRD\_VIE=' FORMES\_VIE' and FORMULE\_VIE = WHOL\_F:

Identification	Type of reference	Value of reference
----------------	-------------------	--------------------

$\Delta \tau(n_1)$	'NON_REGRESSION'	1.1557902030140E+02
component $x$ of $n_1$	'NON_REGRESSION'	3.8280107156988E-01
component $y$ of $n_1$	'NON_REGRESSION'	8.4447216637038E-01
component $z$ of $n_1$	'NON_REGRESSION'	3.7460659341591E-01
$N_{\max}(n_1)$	'NON_REGRESSION'	7.3701737537055E+01
$N_m(n_1)$	'NON_REGRESSION'	-6.6290480086559E+00
$\varepsilon_{\max}(n_1)$	'NON_REGRESSION'	0.
$\varepsilon_m(n_1)$	'NON_REGRESSION'	-4.2254262706848E-05
$\sigma_{eq}(n_1)$	'NON_REGRESSION'	2.8392113675768E+02
$Nb_{cr}(n_1)$	'NON_REGRESSION'	2.0270E+04
$ENDO(n_1)$	'NON_REGRESSION'	4.933357265479E-05
$\Delta \tau(n_2)$	'NON_REGRESSION'	1.1520977056656E+02
component $x$ of $n_2$	'NON_REGRESSION'	-9.1924333354254E-01
component $y$ of $n_2$	'NON_REGRESSION'	3.9019564505737E-01
component $z$ of $n_2$	'NON_REGRESSION'	5.2335956242944E-02
$N_{\max}(n_2)$	'NON_REGRESSION'	1.1296755026397E+02
$N_m(n_2)$	'NON_REGRESSION'	6.8110853707598E+00
$\varepsilon_{\max}(n_2)$	'NON_REGRESSION'	3.6085283407484E-04
$\varepsilon_m(n_2)$	'NON_REGRESSION'	4.5106604259354E-05
$\sigma_{eq}(n_2)$	'NON_REGRESSION'	3.4226598124581E+02
$Nb_{cr}(n_2)$	'NON_REGRESSION'	1.01240E+04
$ENDO(n_2)$	'NON_REGRESSION'	9.8775850589871E-05

For loading not-periodical:

For the results **with the node N214** for the option COURBE\_GRD\_VIE=' WOHLER' and for the option COURBE\_GRD\_VIE=' FORMES\_VIE' and FORMULE\_VIE = WHOL:

Identification	Type of reference	Value of reference
component $x$ of $n_1$	'NON_REGRESSION'	3.8280107156988E-01
component $y$ of $n_1$	'NON_REGRESSION'	8.4447216637038E-01
component $z$ of $n_1$	'NON_REGRESSION'	3.7460659341591E-01

$ENDO(n_1)$	'NON_REGRESSION'	9.2779623136707E-05
-------------	------------------	---------------------

For the results **with the node N206** and with **mesh M60 (not Gauss 3)** for the option COURBE\_GRD\_VIE= 'FORMES\_VIE' and FORMULE\_VIE = WHOL\_F:

Identification	Type of reference	Value of reference
component $x$ of $n_1$	'NON_REGRESSION'	3.8280107156988E-01
component $y$ of $n_1$	'NON_REGRESSION'	8.4447216637038E-01
component $z$ of $n_1$	'NON_REGRESSION'	3.7460659341591E-01
$ENDO(n_1)$	'NON_REGRESSION'	6.1692384350833E-05

## 6 Modeling D

### 6.1 Characteristics of modeling

The features tested are new sizes (which are not part of the criteria existing already tested in other modelings). Only the option CRITERE='FORMULE\_CRITERE' order CALC\_FATIGUE and the curve of life called by the name 'WOHLER' are used.

It is noted that the behavior is elastoplastic and the loading is uniaxial and periodic.

### 6.2 Characteristics of the grid

The grid is identical to that of modeling A.

### 6.3 Sizes tested and results

For the results with the node *NI* and with mesh *M60* :

Identification	Type of reference	Value of reference
'DEPSPE'	'ANALYTICAL'	7.5E-4
'EPSPRI'	'ANALYTICAL'	7.625E-4
'SIGNM1'	'ANALYTICAL'	200
'APHYDR'	'ANALYTICAL'	66.6666
'DENDIS'	'ANALYTICAL'	0.45
'DENDIE'	'ANALYTICAL'	0.173333
'DSIGEQ'	'ANALYTICAL'	200
'EPSNM1'	'ANALYTICAL'	1.75E-3
'INVA2S'	'ANALYTICAL'	1.616666E-3
'DSITRE'	'ANALYTICAL'	50
'DEPTRE'	'ANALYTICAL'	6.0625E-4
'DEPTRE'	'ANALYTICAL'	3.67423E-3
'DEPSEE'	'ANALYTICAL'	0.000866666666

## 7 Modeling E

### 7.1 Characteristics of modeling

The features tested are new sizes.  
It is noted that the behavior is elastoplastic and the loading is biaxial and not-periodical.

### 7.2 Characteristics of the grid

The grid is identical to that of modeling A.

### 7.3 Sizes tested and results

The value of reference corresponds to the endommagement (ENDO1) and the results were got **with the node** *NI* and with **mesh** *M60* via **formula of Basquin** :

Identification	Type of reference	Value of reference
<b>Criteria</b>		
$\frac{ SIPR1 - SIPR2 }{2}$	'ANALYTICAL'	1.0707149E-03
$\frac{ SITN1 - SITN2 }{2}$	'ANALYTICAL'	1.0707149E-03
$\frac{SIPN1 - SIPN2}{2}$	'ANALYTICAL'	1.0707149E-03
$\frac{SIGEQ1 - SIGEQ2}{2}$	'ANALYTICAL'	4.287285E-03

The value of reference always corresponds to the damage (ENDO1) and the results were got **with node** *NI* and with **mesh** *M60* with one **interpolation** curve of Wöhler :

Identification	Type of reference	Value of reference
<b>Criteria</b>		
$\frac{ SIPR1 - SIPR2 }{2}$	'ANALYTICAL'	1.9212572E-03
$\frac{ SITN1 - SITN2 }{2}$	'ANALYTICAL'	1.9212572E-03
$\frac{SIPN1 - SIPN2}{2}$	'ANALYTICAL'	1.9212572E-03
$\frac{SIGEQ1 - SIGEQ2}{2}$	'ANALYTICAL'	5.8175699E-03



## 8 Modeling F

### 8.1 Characteristics of modeling

The features tested are new sizes.

It is noted that various behaviors and loading are tested: rubber band, biaxial and elastoplastic, uniaxial not-periodical then and not-periodical.

### 8.2 Characteristics of the grid

The grid is identical to that of modeling A.

### 8.3 Sizes tested and results

- Result got with the first loading ( `SOL_NL` ):

The value of reference corresponds to the damage (ENDO1) and the results were got **with the node** *NI* and with **mesh** *M60* via **formula of Basquin** :

Identification	Type of reference	Value of reference
<b>Criteria</b>		
$\frac{ EPSN1 - EPSN2 }{2}$	'ANALYTICAL'	1.08363973E-05
$\frac{ ETPR1 - ETPR2 }{2}$	'ANALYTICAL'	1.0 8363973 E-0 5
$\frac{ ETEQ1 - ETEQ2 }{2}$	'ANALYTICAL'	1.06338423E-05

The value of reference always corresponds to the damage (ENDO1) and the results were got **with node** *NI* and with **mesh** *M60* with one **interpolation** curve of Wöhler :

Identification	Type of reference	Value of reference
<b>Criteria</b>		
$\frac{ EPSN1 - EPSN2 }{2}$	'ANALYTICAL'	3.26558686E-05
$\frac{ ETPR1 - ETPR2 }{2}$	'ANALYTICAL'	3.26558686E-05
$\frac{ ETEQ1 - ETEQ2 }{2}$	'ANALYTICAL'	3.21404432E-05



- Result got with the second loading ( **SOL\_NL2** ):  
The value of reference corresponds to the damage (ENDO1) and the results were got **with the node NI** and with **mesh M60** via **formula of Basquin** :

Identification	Type of reference	Value of reference
Criteria		
$\frac{ EPSN1 - EPSN2 }{2}$	'ANALYTICAL'	1.449229E-04
$\frac{ ETPR1 - ETPR2 }{2}$	'ANALYTICAL'	1.449229 E-0 4
$\frac{ ETEQ1 - ETEQ2 }{2}$	'ANALYTICAL'	6.5320499E-05

The value of reference always corresponds to the damage (ENDO1) and the results were got **with node NI** and with **mesh M60** with one **interpolation** curve of Wöhler :

Identification	Type of reference	Value of reference
Criteria		
$\frac{ EPSN1 - EPSN2 }{2}$	'ANALYTICAL'	2.408735E-04
$\frac{ ETPR1 - ETPR2 }{2}$	'ANALYTICAL'	2.408735 E-0 4
$\frac{ ETEQ1 - ETEQ2 }{2}$	'ANALYTICAL'	1.322816E-04

- Result got with the third loading ( **SOL\_NL3** ):  
The value of reference corresponds to the damage (ENDO1) and the results were got **with the node NI** and with **mesh M60** via **formula of Basquin** :

Identification	Type of reference	Value of reference
Criteria		
$\frac{ EPPR1 - EPPR2 }{2}$	'ANALYTICAL'	1.377855E-02

The value of reference always corresponds to the damage (ENDO1) and the results were got **with node NI** and with **mesh M60** with one **interpolation** curve of Wöhler :

Identification	Type of reference	Value of reference
Criteria		
$\frac{ EPPR1 - EPPR2 }{2}$	'ANALYTICAL'	2.1858445E-03

# Code\_Aster

Version  
default

Titre : SSLV135 – Critères d'amorçage en fatigue sous char[...]  
Responsable : PLESSIS Sarah

Date : 21/10/2013 Page : 42/48  
Clé : V3.04.135 Révision :  
ec42efa9db29

--	--	--

## 9 Modeling G

### 9.1 Characteristics of modeling

The features tested are new sizes.

It is noted that various behaviors and loading are tested: an elastic material and an elastoplastic material.

### 9.2 Characteristics of the grid

The grid is identical to that of modeling A.

### 9.3 Sizes tested and results

- Criteria of `DANG_VAN_MODI_AC`, of `MATAKE_MODI_AC`, of `DANG_VAN_MODI_AV`  
For the results of  $\phi_z$  with the node `NI` for an elastic material.

Value of $\alpha$	Type of reference	Value of reference
-1,-0.5,0..10	'ANALYTICAL'	45

For the results of  $\phi_z$  with the node `NI` for an elastoplastic material.

Value of $\alpha$	Type of reference	Value of reference
0,1,2,3,4	'ANALYTICAL'	45

- Criterion of `MATAKE_MODI_AV`

Value of $\alpha$	Type of reference	Value of reference
-1	'ANALYTICAL'	45
-0.5	'ANALYTICAL'	45,72
0	'ANALYTICAL'	46,43
0,5	'ANALYTICAL'	47,14
1	'ANALYTICAL'	47,86
1,5	'ANALYTICAL'	48,56
2	'ANALYTICAL'	49,27
2,5	'ANALYTICAL'	49,96
3	'ANALYTICAL'	50,65
3,5	'ANALYTICAL'	51,34
4	'ANALYTICAL'	52,02
4,5	'ANALYTICAL'	52,69
5	'ANALYTICAL'	53,35
5,5	'ANALYTICAL'	54
6	'ANALYTICAL'	54,65
6,5	'ANALYTICAL'	55,28

7	'ANALYTICAL'	55,9
7,5	'ANALYTICAL'	56,51
8	'ANALYTICAL'	57,11
8,5	'ANALYTICAL'	57,7
9	'ANALYTICAL'	58,28
9,5	'ANALYTICAL'	58,85
10	'ANALYTICAL'	59,41

For the results of  $\phi_z$  with the node *NI* for an elastoplastic material.

Value of $\alpha$	Type of reference	Value of reference
0	'ANALYTICAL'	46,43
1	'ANALYTICAL'	47,86
2	'ANALYTICAL'	49,27
3	'ANALYTICAL'	50,65
4	'ANALYTICAL'	52,02

- **Criterion of FATESOCI\_MODI\_AV**

For the results of  $\phi_z$  with the node *NI* for an elastic material.

Value of $\alpha$	Type of reference	Value of reference
-1	'ANALYTICAL'	45
-0,5	'ANALYTICAL'	45,34
0	'ANALYTICAL'	45,67
0,5	'ANALYTICAL'	45,99
1	'ANALYTICAL'	46,31
1,5	'ANALYTICAL'	46,61
2	'ANALYTICAL'	46,91
2,5	'ANALYTICAL'	47,2
3	'ANALYTICAL'	47,48
3,5	'ANALYTICAL'	47,75
4	'ANALYTICAL'	48,01
4,5	'ANALYTICAL'	48,27
5	'ANALYTICAL'	48,51
5,5	'ANALYTICAL'	48,75
6	'ANALYTICAL'	48,98
6,5	'ANALYTICAL'	49,2
7	'ANALYTICAL'	49,42

7,5	'ANALYTICAL'	49,63
8	'ANALYTICAL'	49,83
8,5	'ANALYTICAL'	50,03
9	'ANALYTICAL'	50,22
9,5	'ANALYTICAL'	50,4
10	'ANALYTICAL'	50,58

For the results of  $\phi_z$  with the node  $NI$  for an elastoplastic material.

Value of $\alpha$	Type of reference	Value of reference
0	'ANALYTICAL'	45,67
1	'ANALYTICAL'	46,31
2	'ANALYTICAL'	46,91
3	'ANALYTICAL'	47,48
4	'ANALYTICAL'	48,01

## 10 Modeling H

### 10.1 Characteristics of modeling

The features tested are new sizes and the keyword `FORMULE_CRITIQUE`. Only the option `CRITERE='FORMULE_CRITERE'` order `CALC_FATIGUE` and the curves of life called by the formulas are used.

It is noted that the behavior is elastoplastic and the loading is uniaxial and periodic.

### 10.2 Characteristics of the grid

The grid is identical to that of modeling A.

### 10.3 Sizes tested and results

For the results with the node `NI` and with mesh `M60` :

Identification	Type of reference	Value of reference
<b>FORMULE_CRITIQUE =</b> 'DTAUCR' or 'MTAUCR'		
'SIGEQ1'	'ANALYTICAL'	100 MPa
'ENDO1'	'ANALYTICAL'	1.028E-6
'NBRUP1'	'ANALYTICAL'	9.73E5
'VNM1X', 'VNM1Y', 'VNM1Z'	'ANALYTICAL'	(0,707, -0,707), 0,707.0
<b>FORMULE_CRITIQUE =</b> 'DGAMCR' or 'MGAMCR'		
'SIGEQ1'	'ANALYTICAL'	9.73E5
'ENDO1'	'ANALYTICAL'	1.583E-4
'NBRUP1'	'ANALYTICAL'	6.3163E3
'VNM1X', 'VNM1Y', 'VNM1Z'	'ANALYTICAL'	(0,707, -0,707), 0,707.0
<b>FORMULE_CRITIQUE =</b> 'DSINCR' or 'MSINCR'		
'SIGEQ1'	'ANALYTICAL'	200
'ENDO1'	'ANALYTICAL'	1.348E-5
'NBRUP1'	'ANALYTICAL'	7.418E4
'VNM1X', 'VNM1Y', 'VNM1Z'	'ANALYTICAL'	(- 1.1), 0.0174,0
<b>FORMULE_CRITIQUE =</b> 'DEPNCR' or 'MEPNCR'		
'SIGEQ1'	'ANALYTICAL'	1.75E-3
'ENDO1'	'ANALYTICAL'	2.11E-5
'NBRUP1'	'ANALYTICAL'	4.74E4
'VNM1X', 'VNM1Y', 'VNM1Z'	'ANALYTICAL'	(- 1, 1), 0.0174,0

<b>FORMULE_CRITIQUE = 'DGAMPC' or 'MGAMPC'</b>		
'SIGEQ1'	'ANALYTICAL'	1.125E-3
'ENDO1'	'ANALYTICAL'	1.3782E-6
'NBRUP1'	'ANALYTICAL'	7.256E5
'VNM1X', 'VNM1Y', 'VNM1Z'	'ANALYTICAL'	(0,707, -0,707), 0,707.0
<b>FORMULE_CRITIQUE = 'DEPNPC' or 'MEPNPC'</b>		
'SIGEQ1'	'ANALYTICAL'	0.75E-3
'ENDO1'	'ANALYTICAL'	1.126E-7
'NBRUP1'	'ANALYTICAL'	8.88E6
'VNM1X', 'VNM1Y', 'VNM1Z'	'ANALYTICAL'	(- 1.1), 0.0174,0

## 11 Summary of the results

---

The got results are in perfect agreement with the reference solution for modeling A. modeling B does not have reference solutions associated with the criteria. Modeling C does not have a reference solution, it acts of a test of not-regression.

The results of modelings D, E, F, G and H agree with the analytical results.